

MSF

by Jayanudin Jayanudin

Submission date: 10-Mar-2023 11:43AM (UTC+0700)

Submission ID: 2033633263

File name: 3._MSF_Jurnal_Internasional_bereputasi.pdf (543.18K)

Word count: 2736

Character count: 15161

Synthesize Fe₃O₄-TiO₂ Composite for Methyl Orange Photocatalytic Degradation

Indar Kustiningsih^{1,2,a*}, Fajariswan Nurrahman^{1,b}, Hazby Ashyra Rinaldi^{1,c},
 Ipah Ema Jumiati^{3,d}, Denni Kartika Sari^{1,e}, Jayanudin^{1,f}

¹Chemical Engineering Department, Universitas Sultan Ageng Tirtayasa

²Nanomaterials and Process Technology Laboratory, Center of Excellence, Faculty of Engineering, Universitas Sultan Ageng Tirtayasa

³Public Administration Department, Social and Political Sciences Faculty, Universitas Sultan Ageng Tirtayasa Jl. Jenderal Sudirman Km.03, Cilegon 42435, Indonesia

^aindar.kustiningsih@untirta.ac.id, ^bfajariswann.fn@gmail.com, ^chazbyrinaldi@gmail.com,
^dema.ipah@untirta.ac.id, ^edenni.kartikasari@untirta.ac.id, ^fjayanudin@untirta.ac.id

Keywords: Composite, Fe₃O₄-TiO₂, Photocatalytic, Degradation, Methyl Orange

Abstract. The effect of Fe₃O₄ percentage on Fe₃O₄-TiO₂ composite for methyl orange photocatalytic degradation has been investigated. Hydrothermal was tried out on TiO₂ before being combined with Fe₃O₄ by precipitation method. The composites were characterized by means of Scanning Electron Microscope (SEM), X-ray diffraction (XRD) and UV-Vis diffuse and reflectance spectroscopy (UV-Vis DRS). The photocatalytic activity of Fe₃O₄-TiO₂ composites were evaluated for methyl orange degradation. The addition of Fe₃O₄ to TiO₂ could reduce the bandgap energy. The lowest bandgap energy was obtained at 20% Fe₃O₄-TiO₂ composite. By using this composite, the degradation of methyl orange was 90%.

Introduction

Most of the textile industry uses synthetic dyes for reasons of cheap, durable, easy to obtain, and easy to use. The use of synthetic textile dyes poses some problems are the waste is still colored and difficult to degrade^[1,2,3]. One of the dyes that are widely used in dyeing process is methyl orange^[4,5]. Several conventional ways of treating textile waste have been developed by researchers including chlorination, ozonation, biodegradation and adsorption. Some weaknesses of this method include high operational costs and relatively difficult to apply in Indonesia^[6].

One alternative to treating textile waste is photocatalyst technology. According to International Union of Pure and Applied Chemistry (IUPAC), photocatalysts are defined as chemical reactions caused by light (photo-absorption) either ultraviolet, visible, or infrared by solid materials namely catalysts that have the ability to absorb photons and are generally owned by materials semiconductor material, the reaction on the semiconductor surface does not change during and after the reaction^[7,8].

The most frequently used and developed semiconductors is TiO₂. TiO₂ has an energy band of 3.2 eV^[9]. The advantages of TiO₂ that have been widely applied include photocatalysts, biomaterials, pigments, solar cells, gas sensors, capacitors, anti-bacterial agents, self-cleaning, drug delivery, anticancer therapies, and in the environment, namely waste degradation^[9-12].

Nanocomposites are nanomaterials that combine one or more components in order to obtain the best properties of each component. The result of nanocomposites can improve the properties that include mechanical strength, toughness, electrical conductivity, chemical resistance, thermal stability, and surface appearance^[13].

The following are some types of TiO₂ nanocomposites, namely modification with charge transfer catalyst (Al₂O₃ and SiO₂), coating with photosensitizing dyes^[3,14], noble metal deposition (Fe, Ag, Au, Pt), doping and grafting (CNT and MWCNT), coupling with semiconductors (semiconductor) CdS, ZnO, WO₃, and modification with polymers (Poly amide, poly-lactic acid, polypyrrole)^[15]. To reduce the loss of catalysts and maintain performance during the separation and recycling process is by adding magnetic properties to the catalyst. Magnetic separation is considered faster and more

effective than traditional separation such as centrifugation and filtration. One material that has magnetic properties is Fe_3O_4 [16]. In this study we proposed the nanocomposite $\text{Fe}_3\text{O}_4\text{-TiO}_2$ by using combination sonication and hydrothermal treatment. The influence of Fe_3O_4 on the photoelectrochemical properties and photocatalytic activity evaluated by methyl orange degradation.

Methodology

Synthesis of TiO_2 for nanocomposite base was carried out by the hydrothermal-sonication method [10]. A total of 3 grams of Degussa P-25 TiO_2 was mixed with 150 ml of 10 M NaOH solution, followed by sonication for 1 hour (120 W). The solution put into an autoclave at 130°C for 12 hours. The resulting sample is washed with a 0.2 N HCl solution to pH 2. Washing continued with water to pH 6 [10]. The next step, the sample was dried at 150°C until the product is completely dry, then calcined for 1 hour at temperature of 500°C . The $\text{Fe}_3\text{O}_4\text{-TiO}_2$ nanocomposite was obtained by the precipitation method. Solution A consists of $\text{FeCl}_3\cdot 6\text{H}_2\text{O}$ and $\text{FeSO}_4\cdot 7\text{H}_2\text{O}$ (2:1) dissolved in 20 ml distilled water to obtain a homogeneous solution. $\text{FeSO}_4\cdot 7\text{H}_2\text{O}$ and $\text{FeCl}_3\cdot 6\text{H}_2\text{O}$ as Fe^{2+} and Fe^{3+} precursors for Fe_3O_4 formation. Solution B consisted of TiO_2 prepared in a solution of distilled water and ethanol (1:1) and ultrasonic for 3 hours to obtain a uniform suspension. Solution A was dropped into solution B, then stirred in a water bath at 80°C for 30 minutes to maintain the temperature. Then add ammonia and stir again for 5 minutes. The mixture transferred to the autoclave at 100°C for 1 hour to form nanocomposite $\text{Fe}_3\text{O}_4\text{-TiO}_2$. The final product was washed with distilled water and dried in the oven. Morphological characterization using Scanning Electron Microscopy (SEM) at LIPI Physics, Serpong. The characterization of catalyst using X-Ray Diffraction (XRD) at the UIN Syarif Hidayatullah Integrated Laboratory Jakarta. To measure bandgap energy using UV-Vis Diffuse Reflectance Spectroscopy (UV-Vis DRS) at the Chemical Services Laboratory, Faculty of Mathematics and Natural Sciences, University of Indonesia. The photocatalytic activity test was carried out in a closed container using a 300 W mercury lamp for 1 hour with sampling intervals every 10 minutes, then to get a decrease in concentration carried out by testing with a spectrophotometer at the Basic Chemistry Laboratory of Sultan Ageng Tirtayasa University.

Result and Discussion

Scanning Electron Microscope Test Results. The sonication treatment causes the solution to appear more homogeneous by forming a white suspension, due to the breakdown of aggregates that exist to the molecular level. In addition, sonication helps break the chemical bonds of TiO_2 in the suspension into Ti-O-Ti bonds which will be easier to react with NaOH so that can be reduce hydrothermal time [4].

In the catalyst leaching process with 0.2 N HCl and distilled water, the Na element exchange from NaOH with hydrogen protons from H_2O that has a smaller atomic size [19]. To increase the crystallinity of the catalyst, calcination was carried out in the furnace at a temperature of 500°C to obtain the anatase crystal structure.

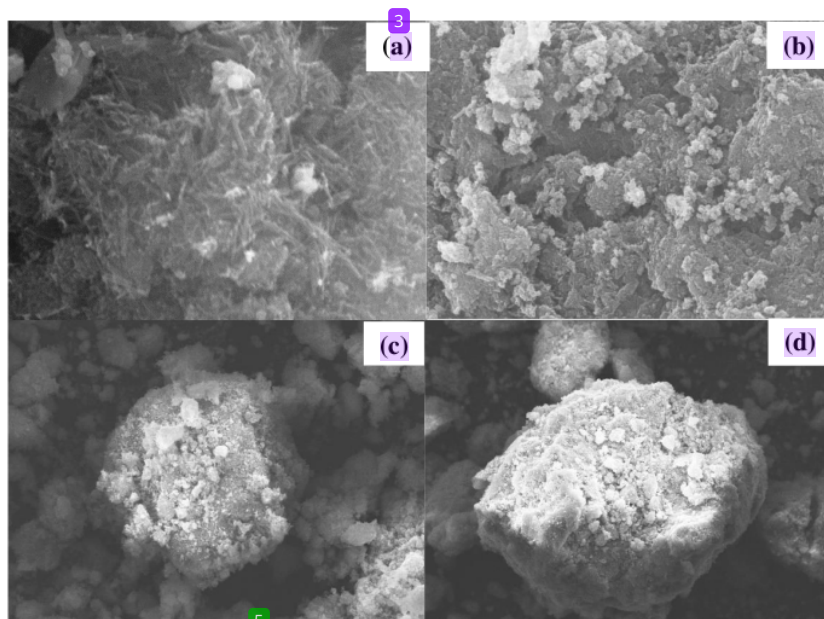


Figure 1. SEM Result of (a) TiO_2 , (b) 10% Fe-TiO_2 , (c) 15% Fe-TiO_2 , and (d) 20% Fe-TiO_2

After going through the hydrothermal - sonication process and SEM analysis, TiO_2 was obtained for the base nanocomposite in the form of nanoparticles (Figure 1). In Figures 1b, 1c, and 1d are the results of SEM analysis of the Fe-TiO_2 nanocomposite photocatalyst. The Fe-TiO_2 nanocomposite was obtained from the second hydrothermal process from the first hydrothermal. From Fig 1, it can be seen that there are Fe_3O_4 nanoparticles attached to the surface of TiO_2 . Figures 1b, 1c and 1d show the results of SEM characterization of nanocomposite photocatalysts with 10% Fe_3O_4 (10 Fe-TiO_2), 15% (15- Fe-TiO_2) and 20% (20 Fe-TiO_2) nanoparticle concentrations.

It can be seen in the figure 1 that when the concentration of Fe_3O_4 nanoparticles increases to 15%, more and more nanoparticles attach to the surface of TiO_2 . However, when the concentration of Fe_3O_4 nanoparticles increases to 20%, there is an aggregation phenomenon and many nanoparticles form larger nanoparticles with rough surfaces. From Figure 1 it can be seen that the addition of Fe_3O_4 nanoparticles does not cause damage to the morphology of TiO_2 but that Fe_3O_4 nanoparticles adhere to and surround the surface of TiO_2 [20].

Characterization of X-Ray Diffraction (XRD). Based on Fig. 2 we can see the XRD pattern of TiO_2 material along with the characteristics of the peaks based on JCPDS card number 21-1272 which shows the diffractogram of TiO_2 obtained is an anatase phase. This can be seen from the value of 2θ obtained, namely 25.42° (101); 38.24° (112); 48.48° (200); 55.26° (211). Figures 2b, 2c and 2d are catalysts synthesized by Fe_3O_4 with different concentrations of 10%, 15% and 20%, in the three figures show that besides the anatase peaks there are also peaks of Fe_3O_4 . Based on JCPDS card number 26-1136, the results of Fe-TiO_2 synthesis containing Fe_3O_4 compounds can be seen from the 2θ values obtained, namely 35.82° (311) and 63.04° (440). In Figures 2b, 2c, and 2d the peaks of Fe_3O_4 vary and show that the greater addition of quantity of a material in this case Fe_3O_4 can affect the peak of the added material will be higher. However, it should be noted also in the addition of quantities of Fe_3O_4 because if too much TiO_2 as a foundation will be covered by Fe_3O_4 and will affect the photocatalytic process.

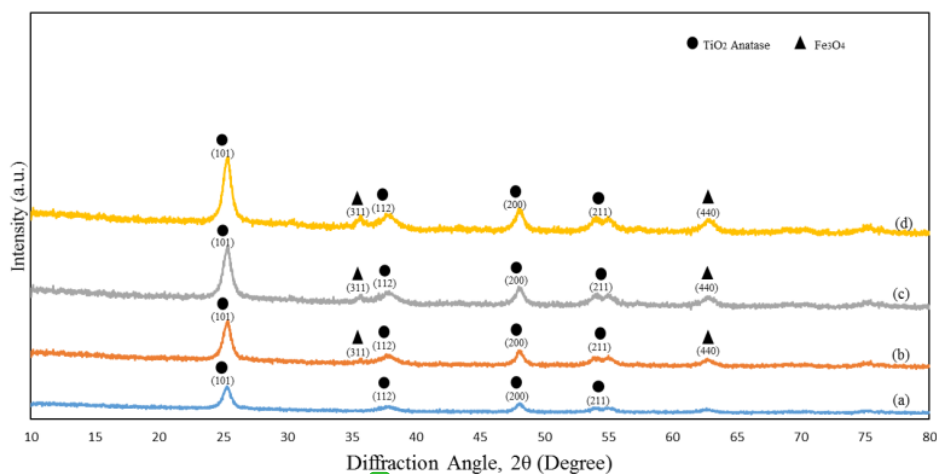


Figure 2. XRD Patterns of catalysts (a) TiO_2 , (b) 10% Fe-TiO_2 , (c) 15% Fe-TiO_2 , (d) 20% Fe-TiO_2 . Determination of particle size is done using the Debye-Scherrer equation as in equation (1).

$$D = \frac{0.9\lambda}{\beta \cos\theta} \quad (1)$$

In the equation (1), λ is the wavelength of the X-Ray (0.1540 nm), β is FWHM (full width at half maximum), θ represents the diffraction angle and D indicates the size of a particle. The value of crystal size calculated using the Debye-Scherrer (equation (1)) is shown in Table 1.

Table 1. Crystallite size of anatase

Catalyst	Anatase Diameter [nm]
TiO_2	92.91
10% Fe-TiO_2	109.122
15% Fe-TiO_2	108.534
20% Fe-TiO_2	104.236

Characterization of UV-Visible Diffuse Reflectance Spectroscopy (UV-Vis DRS). The UV-Vis DRS for can be seen in Fig. 3. Fig. 3 shows that the wavelength for TiO_2 is 383 nm, $\text{Fe}_3\text{O}_4\text{-TiO}_2$ with a concentration of 10% by 363 nm, $\text{Fe}_3\text{O}_4\text{-TiO}_2$ with a concentration of 15% by 365 nm, $\text{Fe}_3\text{O}_4\text{-TiO}_2$ with a concentration of 20% is 366 nm.

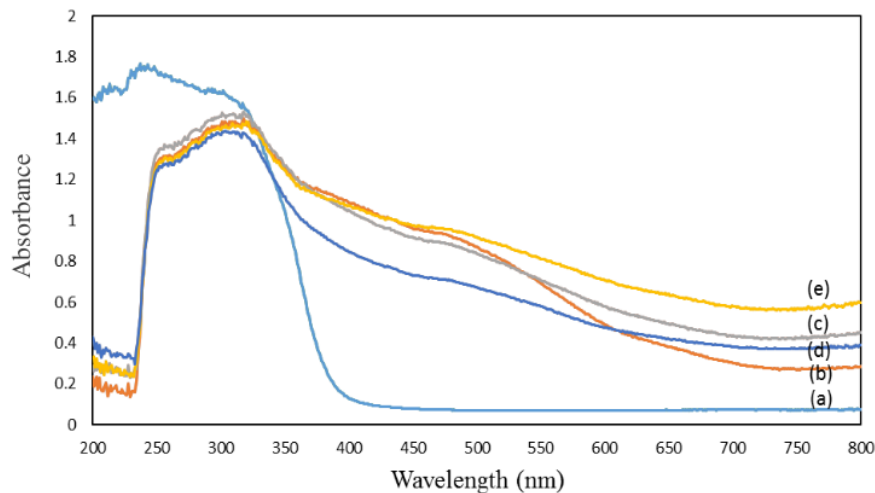


Figure 3. UV-Visible absorption spectra of the catalysts (a) TiO_2 (b) 10% Fe- TiO_2 , (c) 15% Fe- TiO_2 , (d) 20% Fe- TiO_2 , (e) Cu@Fe- TiO_2



From these data it can be seen that TiO_2 and Fe_3O_4 - TiO_2 photocatalysts with concentrations of 10%, 15% and 20% have similar response characteristics to rays, all of which can respond to rays with wavelengths <400 nm. Based on the UV-Vis DRS pattern, it can also be determined the bandgap energy level of the photocatalyst using the Tauc's relation formula. The bandgap energy of samples are shown in Table 2.

Table 2. Catalyst Energy Bandgap

Catalyst	Bandgap Energy [eV]
TiO_2	3.26
10% Fe- TiO_2	2.92
15% Fe- TiO_2	2.85
20% Fe- TiO_2	2.81

Photocatalytic Activity. The methyl orange degradation was carried out by irradiation using a 300 W mercury lamp for 1 hour at intervals every 10 minutes. The initial concentration of methyl orange tested was 4 ppm and a wavelength of 464 nm was obtained which was tested with a UV-Vis Spectrophotometer. The result of methyl orange degradation can be seen at Fig. 4.

The photocatalytic activity of methyl orange degradation results obtained were 20% Fe- TiO_2 (44.23%) > 15% Fe- TiO_2 (24.13%) > TiO_2 (18.40%) > 10% Fe- TiO_2 (17.01%). Figure 4 shows most of the maximum degradation is achieved in 40 minutes. After going through the maximum catalyst time to degrade there is no significant decrease even some have increased again because the absorption of the catalyst was saturated and the catalyst quantity also decreases due to sampling every minute because the sample is in the form of powder and can easily be carried away when taking which sample proven by the moment of separation with a centrifuge there are catalyst deposits. While TiO_2 degradation process still takes place within 60 minutes and is likely to be able to degrade but requires a relatively long time. In the first 10 minutes can be seen from Figure 4 shows that most of the catalyst is working optimally to degrade in the first 10 minutes this is shown by the drastic reduction of some catalysts such as 15% Fe- TiO_2 and 20% Fe- TiO_2 .

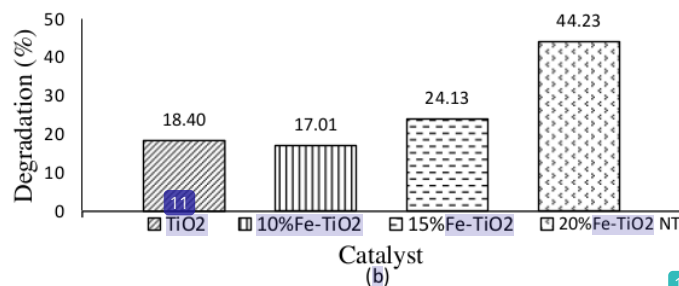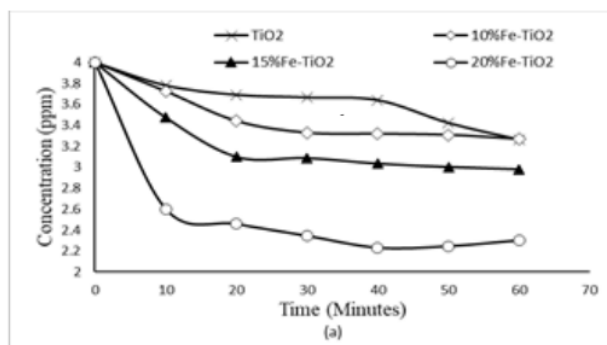

16

Figure 4. Degradation of methyl orange using the samples (a) for 60 minutes (b) % Degradation of methyl orange

16

Conclusion

In this study TiO₂ photocatalysts for nanocomposite bases were obtained by sonication - hydrothermal method. Fe-TiO₂ nanocomposite photocatalyst in the form of nanoparticles and nanocomposite photocatalyst has magnetic properties. Bandgap energy of TiO₂, 10% Fe-TiO₂, 15% Fe-TiO₂, 20% Fe-TiO₂, respectively is 3.26 eV; 2.92 eV; 2.85 eV; 2.81 eV. This photocatalyst has a high enough activity to degrade color waste by 44.23% for 60 minutes.

Acknowledgment

The authors would like to thank to the Universitas Sultan Ageng Tirtayasa under Hibah Penelitian Dasar 2019.

References

- [1] Amalina, E., Harjito & Priatmoko, S., 2016. Effect N – Doping on TiO₂ Photocatalytic Activity for Methyl Orange Degradation. *Indo. J. Chem. Sci.*, Volume 5, pp. 2252-6951.
- [2] Bokare, A. et al., 2014. Hydrothermal Synthesis of Ag@TiO₂ – Fe₃O₄ nanocomposite using sonochemically active precursors : magnetic, photocatalytic, and antibacterial properties. *Materials Research Express*, 1(4).
- [3]. Pujiastuti, H., et al., 2021. Improvement of the Efficiency of TiO₂ Photocatalysts with Natural Dye Sensitizers Anthocyanin for the Degradation of Methylene Blue:Review. *Jurnal Rekayasa Kimia dan Lingkungan*, Volume 16 No 2, pp. 84-99
- [4] Burda, C. et al., 2004. Enhanced nitrogen doping in TiO₂ nanoparticles. *Nano Letters*, Volume 10, pp. 1049-1051.

- [5] Jia, X., Dai, R., Lian, D. & Han, S., 2016. Facile Synthesis and Enhanced Magnetic Photocatalytic Properties of One-Dimensional Ag@Fe₃O₄-TiO₂. *Applied Surface Science*, Volume 392, pp. 268-276.
- [6] Kustiningsih, I. et al., 2011. The Influence of TiO₂ Morphology and Doped PT on Hydrogen Production From Water with Photocatalytic Method. *Indonesian Journal of Materials Science*, Volume 14, pp. 11-16.
- [7] Kustiningsih, I. et al., 2020. Photocatalytic Degradation of Methyl Violet Using TiO₂-Bayah Natural Zeolite Photocatalyst. *J. Environ. Chem. Eng.*, Volume 15, pp. 10-20.
- [8] Kustiningsih, I. et al., 2019. Development of Chitosan - TiO₂ Nanocomposite for Packaging Film and its Ability to Inactivate Staphylococcus aureus. *Oriental Journal of Chemistry*, 35(3), pp. 1132-1137.
- [9] Kustiningsih, I. et al., 2020. *Photocatalytic Degradation of Organic Waste in Visible light using TiO₂ Nanotubes Array*. Serang, Universitas Sultan Ageng Tirtayasa., p. 796:012060.
- [10] Kustiningsih, I., S. & Purwanto, W. W., 2015. Synthesis of TiO₂ Nanotubes by Using Combination of Sonication and Hydrothermal Treatment and Their Photocatalytic Activity for Hydrogen Evolution. *Reaktor*, 15(3), pp. 205-215.
- [11] Kustiningsih, I. et al., 2018. Optimization of TiO₂ Nanowires Synthesis using Hydrothermal Method for Hydrogen Production. *J. Mech. Eng. Sci.*, Volume 12, pp. 3876-3887.
- [12] Matthiew, P., 2016. An Introduction to Photocatalysis Through Methylene Blue Photodegradation. *European Journal of Physics*, 37(6), p. 065808.
- [13] Naimah, S. et al., 2014. Degradasi Zat Warna pada Limbah Cair Industri Tekstil dengan Metode Fotokatalitik Menggunakan Nanokomposit TiO₂ – Zeolit. *J. Electron Package*, 36(2), pp. 225-236.
- [14] Hasanah, E., U., Recent Development and Application of TiO₂ Photocatalytic Activity for Degradation Synthetic Dyes- A Review, *Jurnal Rekayasa Kimia dan Lingkungan*, Volume 16 No 2, pp. 52-67
- [15] Ruzicka, O. & Safira, L., 2014. *Application of TiO₂ Photocatalyst in Degradation of Textile Liquid Dyes*. s.l., s.n.
- [16] Slamet, et al., 2018. Synthesis and Characterization of Magnetically Modified Composites (TiNT/CNT/Fe₃O₄). *Journal of Physics Conference Series*, 1091(1), p. 012024.
- [17] Sulaiman, F., Kustiningsih, I. & Sari, D., 2017. *The Influence of Ozone on the Photocatalytic Degradation of Phenol using TiO₂ Photocatalyst Supported by Bayah Natural Zeolite*. Cilegon, AIP Conference Proceedings.
- [18] Zhang, D. et al., 2013. Two-phase hydrothermal synthesis of TiO₂-graphene hybrids with improved photocatalytic activity. *Journal of Alloys and Compounds*, Volume 572, pp. 199-204.
- [19] Zhang, P., Mo, Z., Wang, Y. & Han, L., 2016. One-Step Hydrothermal Synthesis of Magnetic Responsive TiO₂ Nanotubes /Fe₃O₄/Graphene Composites With Desirable Photo Catalytic Properties and Reusability. *One-step hydrothermal synthesis of magnetic responsive TiO₂ nanotubes/Fe₃O₄/graphene composites with desirable photocatalytic properties and reusability*, 6(45).
- [20] Zhu, C. L. et al., 2010. Fe₃O₄/ TiO₂ core/shell nanotubes: Synthesis and magnetic and electromagnetic wave absorption characteristics. *J Phys Chem C*, 114(39), pp. 16229-16235.

18%

SIMILARITY INDEX

9%

INTERNET SOURCES

16%

PUBLICATIONS

4%

STUDENT PAPERS

PRIMARY SOURCES

- 1** Felisca Melin Dianes, Muhammad R. Ryan, Muhammad Rafli Supriadi, Reyza Halim, Yanuar Nugraha, Alfirano. "Improving Surface Hardness of AISI H13 Steel by Pack Nitriding", Materials Science Forum, 2022
Publication 2%
- 2** Xiaohua Jia, Rongrong Dai, Dandan Lian, Song Han, Xiangyang Wu, Haojie Song. "Facile synthesis and enhanced magnetic, photocatalytic properties of one-dimensional Ag@Fe₃O₄-TiO₂", Applied Surface Science, 2017
Publication 2%
- 3** pu.edu.pk
Internet Source 2%
- 4** repository.unej.ac.id
Internet Source 2%
- 5** Qi, G.. "Low-temperature selective catalytic reduction of NO with NH₃ over iron and manganese oxides supported on titania", Applied Catalysis B, Environmental, 20030830 1%

6	www.ijsred.com Internet Source	1 %
7	jmes.ump.edu.my Internet Source	1 %
8	H Zhang, R L Liu. " Study on properties of electroless (Ni-P)-Fe O (nanometre) composite plated PET fabrics ", Surface Engineering, 2013 Publication	1 %
9	pubs.rsc.org Internet Source	1 %
10	Linda Jati Kusumawardani, Ani Iryani, Eka Yulianti. "Photocatalytic decolorization of methylene blue using TiO ₂ -Fe photocatalyst under visible and sunlight irradiation", AIP Publishing, 2022 Publication	1 %
11	Teoh, Wey. "A Perspective on the Flame Spray Synthesis of Photocatalyst Nanoparticles", Materials, 2013. Publication	1 %
12	Erlina Yustanti, Muhammad Zuhdi Syihab, Latifa Hanum Lalasari, Azwar Manaf. "Synthesis of TiO ₂ from TiOSO ₄ Solution with Sonochemical Method", Materials Science Forum, 2022	1 %

13 doaj.org 1 %
Internet Source

14 Pabika Salsabila Witri, Rahmayetty
Rahmayetty, Muhamad Toha, Alamsyah,
Nufus Kanani, Endarto Y. Wardhono. 1 %
"Acetylation of Bacterial Cellulose from a
Mixture of Palm Flour Liquid Waste and
Coconut Water: The Effect of Acetylation Time
on Yield and Identification of Cellulose
Acetate", Materials Science Forum, 2022
Publication

15 Submitted to Anglia Ruskin University 1 %
Student Paper

16 Raja Azadar Hussain, Syed Hamza Safeer. 1 %
"Low temperature synthesis of iron selenide
by thermolysis of organometallic precursor
for photodegradation under direct sunlight",
Results in Chemistry, 2022
Publication

17 Submitted to Universiti Malaysia Kelantan 1 %
Student Paper

18 repository.lppm.unila.ac.id 1 %
Internet Source

Exclude quotes On

Exclude matches < 1%

Exclude bibliography On

MSF

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7
