

# Utilization of fly ash and bottom ash to increase the value of unconfined compression strength on subgrade

*by* Penulis 1 Penulis 2

---

**Submission date:** 27-Mar-2023 09:32AM (UTC+0700)

**Submission ID:** 2047454820

**File name:** 16307-49527-1-PB-1.pdf (349.95K)

**Word count:** 4473

**Character count:** 21597



19

TEKNIKA: JURNAL SAINS DAN TEKNOLOGI

Homepage jurnal: <http://jurnal.untirta.ac.id/index.php/ju-tek/>

## Utilization of fly ash and bottom ash to increase the value of unconfined compression strength on subgrade

Woelandari Fathonah<sup>a,1</sup>, Rama Indera Kusuma<sup>a</sup>, Enden Mina<sup>a</sup>, Restu Wigati<sup>a</sup>, Dwi Esti Intari<sup>a</sup>,  
Nada Shafa Soraya Gandakusumah<sup>a</sup>

<sup>9</sup><sup>a</sup>Department of Civil Engineering, Faculty of Engineering, Universitas Sultan Ageng Tirtayasa, Jl. Jenderal Sudirman Km 3, Cilegon City, Banten 42435, Indonesia

<sup>1</sup>Corresponding Author: [woelandari@untirta.ac.id](mailto:woelandari@untirta.ac.id)

### ARTICLE INFO

#### Article history:

Submitted 04 April 2022

Received 05 April 2022

Received in revised form 06 June 2022

Accepted 30 September 2022

Available online on 30 November 2022

#### Keywords:

Bottom ash, fly ash, unconfined compression strength test.

#### Kata kunci:

Bottom ash, fly ash, kuat tekan bebas.

### ABSTRACT

Soil is the most important part to support all traffic loads or construction loads placed on it. Soils that have low bearing capacity, such as clay, need stabilization techniques to increase the carrying capacity of the soil. One of the stabilization techniques is to mix the soil with Fly ash and Bottom ash. The purpose of this study was to determine the effect of Fly ash and Bottom ash on the physical properties of the soil and the value of unconfined compression strength test. The variations of Fly ash and Bottom ash used were Fly ash 0% and 20% and variations of Bottom ash 0%, 10%, 20% and 30% with curing time of 0, 7, 14 and 28 days. Soil is classified according to the Unified Soil Classification System (USCS) method. The results showed that the soil classification was classified as OH, namely organic clay with plasticity of 21.08%. The results of the unconfined compression strength test show that the addition of fly ash and bottom ash increases the  $q_u$  value of the clay soil. The optimum  $q_u$  value was obtained at variation B (Bottom ash 10% and Fly ash 20%) with 28 days curing time of 2.994 kg/cm<sup>2</sup>. The decrease in the value of  $q_u$  occurred in variation C (Bottom ash 20% and Fly ash 20%) and variation D (Bottom ash 30% and Fly ash 30%). Soil with the addition of 0% and 20% Fly ash and Bottom ash at variations of 0%, 10%, 20% and 30% showed a decrease in the value of the soil plasticity index from 21.083% to 7.511%.

### ABSTRAK

Tanah merupakan bagian yang terpenting untuk mendukung seluruh beban lalu lintas atau beban konstruksi yang ditempatkan di atasnya. Tanah yang memiliki daya dukung rendah seperti tanah lempung, perlu dilakukan teknik stabilisasi untuk meningkatkan daya dukung tanah tersebut. Salah satu teknik stabilisasi yaitu melakukan pencampuran tanah dengan Fly ash dan Bottom ash. Tujuan penelitian ini adalah untuk mengetahui pengaruh Fly ash dan Bottom ash terhadap sifat fisik tanah dan nilai kuat tekan bebas variasi Fly ash dan Bottom ash yang digunakan yaitu Fly ash 0% dan 20% serta variasi Bottom ash 0%, 10%, 20% dan 30% dengan lama pemeraman 0, 7, 14 dan 28 hari. Tanah diklasifikasikan berdasarkan metode Unified Soil Classification System (USCS). Hasil penelitian menunjukkan klasifikasi tanah termasuk ke dalam jenis OH yaitu tanah lempung organik dengan plastisitas tinggi sebesar 21.08%. Hasil pengujian kuat tekan bebas menunjukkan penambahan Fly ash dan bottom ash meningkatkan nilai  $q_u$  tanah lempung. Nilai  $q_u$  optimum diperoleh pada variasi B (Bottom ash 10% dan Fly ash 20%) dengan lama pemeraman 28 hari sebesar 2.994 kg/cm<sup>2</sup>. Penurunan nilai  $q_u$  terjadi pada variasi C (Bottom ash 20% dan Fly ash 20%) dan variasi D (Bottom ash 30% dan Fly ash 30%). Tanah dengan penambahan 0% dan 20% Fly ash dan Bottom ash pada variasi 0%, 10%, 20% dan 30% menunjukkan adanya penurunan nilai indeks plastisitas tanah dari 21.083% menjadi 7.511%.

12

Available online at <http://dx.doi.org/10.36055/tjst.v18i1.16307>



13

Teknika: Jurnal Sains dan Teknologi is licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 4.0 International License.

## 1. Introduction

In building a road, soil is the most important part to support the entire traffic load or construction load placed on it. Therefore, in planning a construction, an investigation must be carried out on the characteristics and strength of the soil, especially the soil properties that affect the bearing strength of the soil in resisting the load of the construction on it. Clay soils generally have soil technical properties such as the bearing capacity of CBR and very low unconfined compression strength [1]. A road pavement structure after being implemented will experience changes in the rainy and dry seasons. In the rainy season, the base layer will experience waterlogging which is a problem that must be overcome [2]. Soil stabilization is a method that aims to improve the basic properties of the soil so that the carrying capacity of the soil becomes more stable and the carrying capacity of the soil becomes greater so that it can withstand the load acting on it [3]. Soil stabilization must be carried out if the soil found in the field is very easily compressed, or if it has an inappropriate consistency index, permeability is too high, or other undesirable properties that are not suitable for a development project [4]. Chemical stabilization is a stabilization that combines an element with another with the aim of getting a new element [5]. The purpose of soil stabilization is to improve the soil in order to obtain a stable subgrade in all conditions. To overcome the problem of soil bearing capacity so that the strength of road construction is appropriate and feasible to use and it is necessary to make efforts to improve soil through soil stabilization efforts [6].

According to developments in the field, soil stabilization technology has improved. One of them is mixing soil with chemicals. One mixture of chemicals that can improve soil quality is fly ash and bottom ash. In the content of fly ash and bottom ash in the form of these chemical compounds, they have a self-hardening property (the ability to harden and to increase strength when reacted with liquids such as water) used on FHWA (2003), utilization of bottom ash can be used as a filler in concrete mixtures, such as to reduce the use of sand material. For this reason, the use of bottom ash can be combined with fly ash in subgrade stabilization as well as for soil improvement. The addition of fly ash can lower the value of the liquid limit and limit plastic [7].

Fly ash is used with alkaline materials and as an activator NaOH and sodium silicate ( $\text{Na}_2\text{SiO}_3$ ) are used so that a polymerization process occurs which can then bind the aggregates [8]. The use of bottom ash can be combined with fly ash in the manufacture of concrete mixtures (structural concrete and road pavement), aggregate foundation layers, subgrade stabilization as well as for soil improvement [9]. Bottom ash is waste ash whose size is larger than fly ash, so bottom ash will fall to the bottom of the furnace (boiler) [10]. Fly ash and bottom ash are solid wastes produced from burning coal in power plants. There are three types of coal burning in the electricity industry, namely dry bottom boilers, wet-bottom boilers, and cyclon furnaces [11].

Bottom ash and fly ash are used as subgrade stabilization agents because they contain quite high silicon dioxide ( $\text{SiO}_2$ ), namely 61.79% ( $\text{SiO}_2$  content in Bottom ash) and 41.96% ( $\text{SiO}_2$  content in Fly ash). The chemical composition of Bottom ash and Fly ash is shown in Table 1.

Table 1. Chemical composition of bottom ash and fly ash

Parameter	Bottom Ash (Lignite or sub-bitumen)	Fly Ash (Class C – sub bitumen)
Loss On Ignition	1.18	0.12
Unburned Carbon	0.02	0.01
Silicon Dioxide ( $\text{SiO}_2$ )	61.79	41.96
Aluminium Trioxide ( $\text{Al}_2\text{O}_3$ )	12.62	21.00
Iron Trioxide ( $\text{Fe}_2\text{O}_3$ )	15.05	16.6
Calcium Oxide ( $\text{CaO}$ )	4.03	11.79
Magnesium Oxide ( $\text{MgO}$ )	1.58	3.06
Potassium Oxide ( $\text{K}_2\text{O}$ )	0.46	0.57
Sodium Oxide ( $\text{Na}_2\text{O}$ )	0.84	0.66
Manganese Dioxide ( $\text{MnO}_2$ )	0.17	0.60
Titan Dioxide ( $\text{TiO}_2$ )	1.33	1.64
Phosphorus Pentaoxide ( $\text{P}_2\text{O}_5$ )	0.54	0.53
Sulfur Trioxide ( $\text{SO}_3$ )	0.95	0.98
Undetermined	0.64	0.61

(Source: PT. Indonesia Power Unit Jasa Pembangunan PLTU Banten 3 Lontar)

Kusuma's research (2017) shows that Fly Ash can increase the value of the unconfined compression strength ( $q_u$ ) of clay soils up to 202.38% with a percentage of 20% Fly Ash mixture [12]. Another study by Monang, L. (2020) showed that BAFA (Bottom Ash and Fly Ash) can increase the value of the unconfined compression strength ( $q_u$ ) of clay with a mixed percentage of 16% [13]. According to Hauashdh, A. (2020) BAFA (Bottom Ash and Fly Ash) shows that this material has cementation features and also confirms the possibility of utilizing coal ash waste as a binder [14]. Zega's research (2020) shows the results that the addition of cement and BAFA in stabilizing high plasticity soft soils can increase the UCS value, which is greatest in soils with 5% cement and 16% BAFA with 28 days curing [13]. The increase in the value of  $q_u$  in the UCS sample was greatest in the variation of the sample A-S5-B16-C28, a value of 94.79 kPa, this increase was 76.57% when compared to the value of  $q_u$  A of 22.04 kPa. Triadi (2020) in his research shows the results that the addition of fly ash to ordinary embankment soil can increase the value of the unconfined compression strength of the original soil by 4.389 kg/cm<sup>2</sup> to 11.600 kg/cm<sup>2</sup> curing for 28 days in a 5% fly ash mixture, so the use of fly ash can be used for stabilization on ordinary embankment soil [15]. Turan (2020) in his research showed the results that the soil gradually increased with increasing levels of fly ash, the parameter of stable soil strength in fly ash variations with 7 and 28 days of curing was much higher than that of stable soil with 1 day of curing [16]. The highest  $q_u$  value was obtained from soil with fly ash content of 20% with a curing time of 28 days which resulted in a  $q_u$  value of 6.118 kg/cm<sup>2</sup>. According to Arrofiq (2016), explaining that from the results of the unconfined compression strength test carried out in the laboratory, the longer the curing time is carried out the higher the value of the unconfined

compression strength, therefore the authors use a curing time of 0 days, 7 days, 14 days, and 28 days [17]. This study aims to determine the effect of Fly ash and Bottom ash on the physical properties of the soil and the value of unconfined compression strength. The variations of Fly ash and Bottom ash used were Fly ash 0% and 20% and variations of Bottom ash 0%, 10%, 20% and 30% with curing time of 0, 7, 14 and 28 days. The use of BAFA (Bottom ash Fly ash) is expected to increase the value of  $q_u$  and decrease the plasticity index of the soil.

## 2. Research Methodology

In this study, bottom ash and fly ash were used which were taken from PT. Indonesia Power Unit PLTU Banten 3 Lontar Generation Services as a material for subgrade stabilization. The soil sample used is distrib soil which is located on Jl. Raya Kadomas, Pandeglang District, Pandeglang Regency, Banten. The research was conducted in several stages, firstly testing the physical properties of the soil and analyzing the grain size to determine the type of soil. Then perform a compaction test to determine the optimum moisture content and maximum dry density of the soil. After that, make the test object with the addition of 0% and 20% Fly Ash percentage variations and 0%, 10%, 20%, and 30% Bottom Ash presentation variations 0, 7, 14, and 28 days. After curing is complete do the Unconfined Compression Strength Test (UCT), or also called the unconfined compression strength test to get the value of the bearing capacity of the soil. In addition to the UCT test, the soil physical properties were also tested to determine the effect of adding BAFA (Bottom Ash and Fly Ash) waste to the physical properties of the soil.

## 3. Result and Discussion

### 3.1. Soil Property Data

In this study, the property data used were secondary data as presented in Table 2.

Table 2. Native soil property

No	Basic Soil Property	Value
1	Specific Gravity (Gs)	2.296
2	Liquid Limit (%)	65.7
3	Plastic Limit (%)	44.62
4	Plastic Index (%)	21.083
5	Optimum Water Content (%)	22
6	Maximum Dry Density ( $g/cm^3$ )	1.978

### 3.2. Analysis of Grain Size Test

Based on the sieve analysis test, it was found that the weight value of the severed soil on sieve no. 200 132, the percent value of passing sieve number 200 was 52.2%, which was greater than 50% as shown in Figure 2.

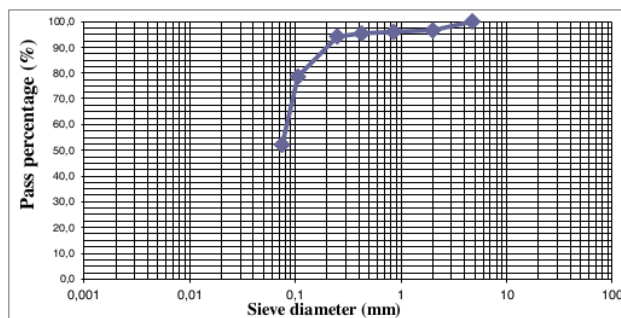


Figure 2. Relationship of percent pass to sieve diameter.

### 3.3. Soil Classification

This soil classification is used to determine the type of soil. Based on the results of the sieve analysis test, the percentage of passing sieve number 200 was >50%. According to the USCS soil classification system, if it passes the sieve number 200 > 50%, then the soil is classified as fine-grained soil. The next classification is seen from the results of the liquid limit and plastic limit tests. Based on the liquid limit test, the result is 66%. The plasticity index value is obtained from the difference between the liquid limit and the plastic limit, which is 21.08%. Referring to the classification system table, the soil is classified

as OH. Therefore, it can be concluded that the type of soil used according to the USCS classification system is OH, namely organic clay with medium to high plasticity. The results are shown in Figure 3.

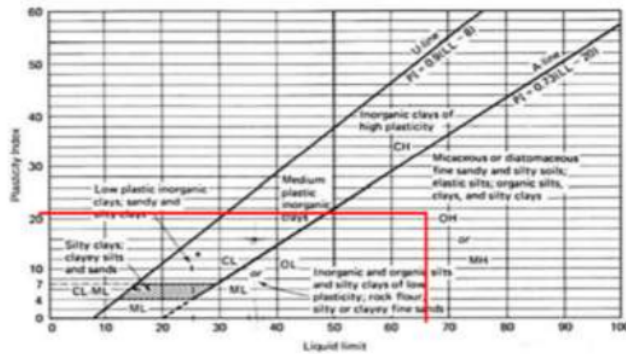


Figure 3. Graph of the relationship between the liquid limit and the plasticity index (Source: Hardiyatmo, 1992) [18].

3.4. Result of Physical Properties of Mixed Soil

Testing of soil physical properties includes soil density test, liquid limit, and plastic limit. The following are the results of these tests:

1. Specific gravity value

Specific gravity values will affect several things such as soil strength, soil self-weight, and determination of sedimentation rate, movement of particles by water and wind. The following are the results of the specific gravity test after mixing.

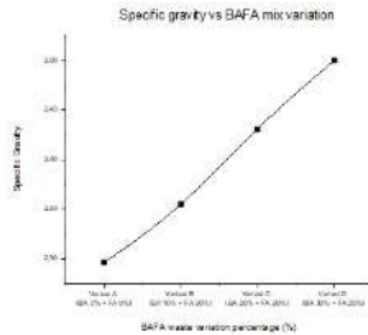


Figure 4. Graph of specific gravity relationship with BAFA variations.

Based on the graph in Figure 4 shows that the addition of bottom ash and fly ash increases the value of the specific gravity of the soil.

2. Liquid limit value

The liquid limit of the soil is the minimum water content at which the properties of a soil change from a liquid state to a plastic state.

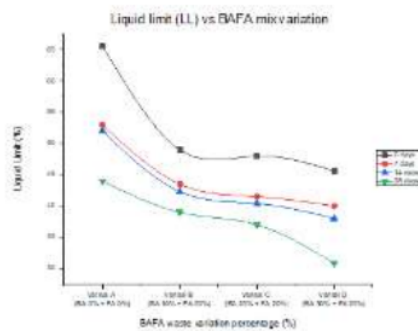


Figure 5. Graph of liquid limit relationship with BAFA variation.

Based on the graph in Figure 5 shows that the liquid limit value decreased with increasing BAFA waste content and with increasing curing time, the liquid limit value with BAFA content and curing time was in the high limit to intermediate limit category.

3. Plastic limit value

8

The plastic limit (PL) is the water content at which a soil changes from a plastic state to a semi-solid state. Plastic limit is calculated based on the percentage of water weight to dry soil weight on the sample soil test.

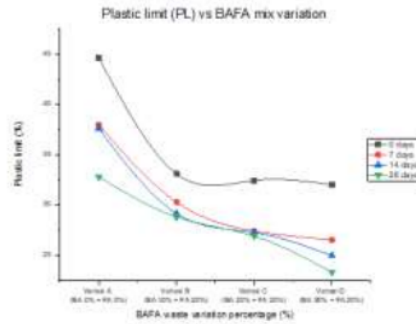


Figure 6. Graph of plastic limit relationship with BAFA variation.

Based on the graph in Figure 6, it shows that the plastic limit value decreased with increasing content of BAFA waste as a soil mixture and similarly with increasing curing time the plastic limit value decreased.

#### 4. Plasticity index

10

Soil Plasticity Index figures were obtained after the Liquid Limit and Plastic Limit tests were completed. Soil Plasticity Index is the difference between the liquid limit (LL) and the plastic limit (PL).

31

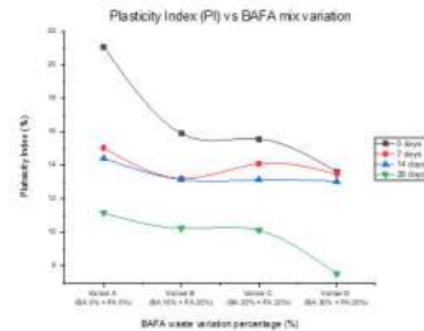


Figure 7. Graph of relationship between plasticity index and BAFA variation.

Based on the graph in Figure 7, it shows that the plasticity index value decreased with increasing BAFA waste content and curing time, which means that the addition of BAFA waste had a good effect on the value of the soil plasticity index on Jalan Raya Kadomas, Pandeglang District, Pandeglang Regency, Banten.

### 3.5. Compaction

16

The compaction test aims to determine the value of the optimum moisture content and maximum dry density of the soil, following are the results of the compaction test:

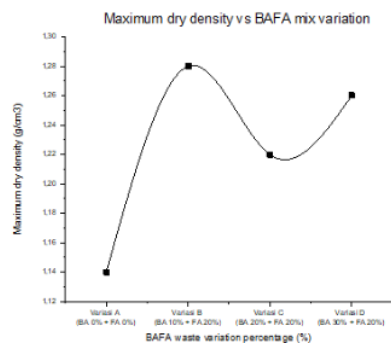


Figure 8. Graph of relationship between maximum dry density and variation of BAFA.

Based on the graph in Figure 8, it shows that the increase in the maximum density value ( $\gamma_d$  max) is due to a change in the particle size of the soil grains which becomes larger/coarser due to the reaction of mixing the soil with coal burning waste (bottom ash and fly ash).

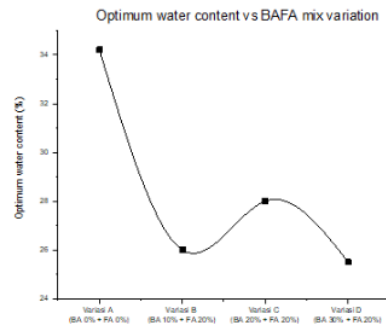


Figure 9. Graph of the relationship between optimum water content and variations in BAFA

Based on the graph in Figure 9 shows that the increase in the value of the optimum water content (wopt) is due when the soil is mixed with coal burning waste (bottom ash and fly ash) and then water is added, a segmentation process (binding) occurs, causing clumping and water content in the soil. land will also increase. Therefore, the greater the addition of BAFA waste, the increase and decrease in the value of the maximum bulk weight and optimum water content will occur.

### 3.6. Unconfined Compression Strength Test

#### 3.6.1. Unconfined Compression Strength Test of Native Soil

The type of soil used is clay soil classification USCS OH. The water content used for the test object is the optimum water content.

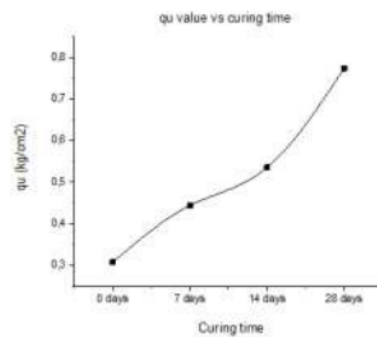


Figure 10. Comparison graph of the original soil qu value against curing time.

Based on Figure 10, it can be seen that the results of the unconfined compression strength test on the original soil produced a maximum qu value of 2.505 kg/cm<sup>2</sup> at 28 days of curing. According to Hardiyatno (1992), the qu value of 2.505 kg/cm<sup>2</sup> of the original soil is classified as very stiff with a qu value of 2 - 4 kg/cm<sup>2</sup> [18].

#### 3.6.2. Comparison of Qu Values with Variations

The following is a comparison of the value of qu with the BAFA variation:

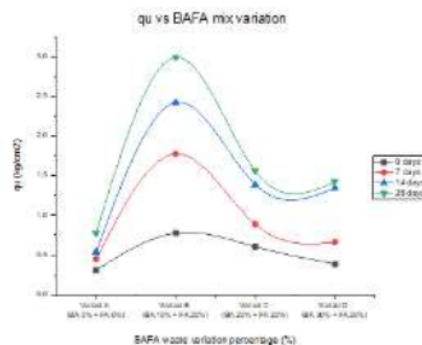


Figure 11. Graph of Relationship between qu value and BAFA variation

Figure 11 shows that the addition of bottom ash and fly ash variations increases the  $q_u$  value until the variation levels of bottom ash are 10% and fly ash is 20%. At the levels of variations in bottom ash 20% and fly ash 20% and variations in bottom ash 30% and fly ash 20% the test specimens decreased so that it can be concluded that the effect of using optimum water content in each mixture on the value of unconfined compression strength makes the value of  $q_u$  more objective, because the water content used in each mixture is the optimum water content in each mixture.

### 3.6.3. Comparison of $Q_u$ Value with Curing Time on Bafa Variation

The following is a comparison of the value of  $q_u$  to the duration of curing

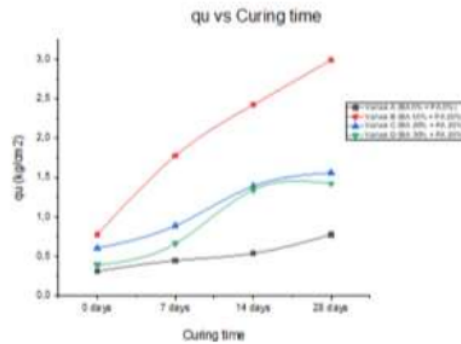


Figure 12. Graph of the relationship between the value of  $q_u$  and curing time.

Figure 12 shows that the value of  $q_u$  always increases with increasing curing time. In all variations of the addition of BAFA waste, 28 days has the greatest value, which means that it can be concluded that the  $q_u$  value of the soil increases due to the pozzolanic nature of BAFA waste so that when mixed with water, the soil will become harder as the curing time increases.

27

## 4. Conclusion

Based on the results of research and testing carried out, it can be concluded that soil stabilization using BAFA (Bottom Ash and Fly Ash) waste on the soil on Jalan Raya Kadomas, Pandeglang District, Pandeglang Regency, Banten, is as follows:

- In testing the physical properties of the original soil, the soil at that location according to the USCS classification system, the soil is included in the OH classification with a plasticity index value of 21.08%, namely organic clay. Because the soil is classified as clay and has high plasticity, it is necessary to improve the soil.
- In the unconfined compression strength test, BAFA waste (Bottom Ash and Fly Ash) can increase the value of the unconfined compression strength which was originally in the original soil condition of 0.740 kg/cm<sup>2</sup> belonging to medium consistency, in variation B (Bottom Ash 10% and Fly Ash 20%) added material with a curing time of 28 days to 2,994 kg/cm<sup>2</sup> is classified as very stiff consistency which is the optimum  $q_u$  value, in variation C (Bottom Ash 20% and Fly Ash 20%) added material with a curing time of 28 days becomes 1,469 kg/cm<sup>2</sup> classified as stiff consistency, and in variation D (Bottom Ash 30% and Fly Ash 20%) added material with a curing time of 28 days became 1.4 kg/cm<sup>2</sup> classified as stiff consistency.
- In this study, BAFA (Bottom Ash and Fly Ash) waste can affect the physical properties of clay. This is indicated by a decrease in the value of the soil plasticity index in the original soil condition of 21.08% which includes high plasticity pure clay, in variation B (Bottom Ash 10% and Fly Ash 20%) with a curing time of 28 days, the plasticity index value becomes 10.23%, in variation C (Bottom Ash 20% and Fly Ash 20%) with a curing time of 28 days the plasticity index value becomes 10.12%, which is a medium plasticity index and belongs to silty clay and in variation D (Bottom Ash 30% and Fly Ash 20%) with a curing time of 28 days, the plasticity index value to 7.511% is a low plasticity index and belongs to the silt soil.
- In this study, taking into account the requirements that apply to the subgrade from the value of  $q_u$  and the value of the plasticity index, what can be used for subgrade improvement is the use of added material B (Bottom Ash 10% and Fly Ash 20%) where the value of  $q_u$  is 2,994 kg/cm<sup>2</sup> and a plasticity index of 10.230% have met the specified requirements.

## REFERENCES

- [1] Situmorang, A. P. P., Hendri, O., & Yani, M. I. (2021). Korelasi nilai hasil uji kuat tekan bebas dengan nilai California Bearing Ratio (CBR) tanah lempung. *J. Ilm. Tek. Sipil TRANSUKMA*, vol. 4, no. 1, pp. 53–60.
- [2] Ariyanto, A. S. (2017). Pengaruh durabilitas terhadap stabilisasi sub base jalan dengan fly ash dari pltu asam asam Kalimantan Selatan, vol. 03, pp. 22–30.
- [3] Insan, M. K., Hariati, F., & Taqwa, F. M. L. (2019). Studi pemanfaatan fly ash dan bottom ash sebagai material stabilisasi tanah dasar (Studi Kasus: pekerjaan subgrade untuk jalan lingkungan di PLTU Sulawesi Utara II, Kabupaten Minahasa Selatan, Sulawesi Utara). *J. Komposit*, vol. 3, no. 2, pp. 1–6, 2019, [Online]. Available: <http://ejournal.uika-bogor.ac.id/index.php/komposit/article/download/3257/1900>.
- [4] Bowles, J. E. (1979). Physical and Geotechnical Properties of Soils.
- [5] Leliana, A., & Andajani, N. (2015). Pengaruh penambahan fly ash terhadap nilai kuat tekan bebas pada tanah lempung ekspansif di daerah Magetan Jawa Timur. *Rekayasa Tek. Sipil*, vol. 1, no. 1, pp. 1–5.



- [6] Fathonah, W., Mina, E., Kusuma, R. I., & Ihsan, D. Y. (2020). Stabilisasi tanah menggunakan semen slag serta pengaruhnya terhadap nilai California Bearing Ratio (CBR) (Studi Kasus: Jl. Munjul, Kp. Ciherang, Desa Pasir Tenjo, Kecamatan Sindang Resmi, Kabupaten Pandeglang). *Jurnal Fondasi*, vol. 9, no. 1, pp. 87-93.
- [7] Mina, E., & Kusuma, R. I. (2016). Pengaruh fly ash terhadap nilai CBR dan sifat-sifat propertis tanah studi kasus: Jalan Raya Bojonegara KM 19 Serang Banten. *Fondasi J. Tek. Sipil*, vol. 5, no. 2, doi: 10.36055/jft.v5i2.1256.
- [8] Kumiasari, P. T. (2017). Pemanfaatan penggunaan fly ash dan bottom ash sebagai pozzolan pada binder geopolimer. Institut Teknologi Sepuluh Nopember.
- [9] Gunawan, G., & Nono. (2019). Potensi pemanfaatan bahan limbah fly ash dan bottom ash untuk lapisan fondasi jalan semen (potential for utilization of fly ash and bottom ash waste materials for cement road foundation). *Jurnal Jalan-Jembatan*, vol. 36, no. 1 Januari-Juni 2019, pp. 19-29.
- [10] Pumama, Y., & Ridwan, M. (2018). Pengaruh penambahan bottom ash pada tanah lempung ekspansif di daerah Lakarsantri Surabaya terhadap nilai daya dukung pondasi dangkal. *Rekayasa Tek. Sipil*, vol. 2, no. 2/REKAT/18, pp. 1-9.
- [11] Wardani, S. P. R. (2008). Pemanfaatan limbah batubara (Fly Ash) untuk stabilisasi tanah maupun keperluan teknik sipil lainnya dalam mengurangi pencemaran lingkungan. Universitas Diponegoro.
- [12] Kusuma, R. I., Mina, E. & Rahman, T. (2016). Stabilisasi tanah dengan menggunakan fly ash dan pengaruhnya terhadap nilai kuat tekan bebas (Studi Kasus Jalan Raya Bojonegara, Kab. Serang). *J. Fondasi*, vol. 5, no. 1.
- [13] Zega, L. M. R. C. (2020). Peningkatan kuat tekan bebas (UCS) tanah lempung (CH) terhadap penambahan limbah BAFA (Bottom Ash & Fly Ash) dan semen. Universitas Riau.
- [14] Hauashdh, A., Mohamed, R. M. S. R., Jailani, J., & Abd Rahman, J. (2020). Stabilization of Peat Soil Using Fly Ash, Bottom Ash and Portland Cement: Soil Improvement and Coal Ash Waste Reduction Approach," *IOP Conf. Ser. Earth Environ. Sci.*, vol. 498, no. 1, 2020, doi: 10.1088/1755-1315/498/1/012011.
- [15] Triadi, D., Rustamaji, R. M., & Aprianto. (2020). Pengaruh penambahan limbah batu bara (Fly Ash) terhadap uji kuat tekan bebas (UCS) pada tanah timbunan biasa. *JeLAST : Jurnal PWK, Laut, Sipil, Tambang*, vol. 7, no. 3, pp. 1-6. Doi. <http://dx.doi.org/10.26418/jelast.v7i3.42578>.
- [16] Turan, C., Javadi, A., Vinai, R., Shariatmadari, N., & Farmani, R. (2020). Use of class C fly ash for stabilization of fine-grained soils. *E3S Web Conf.*, vol. 195, pp. 4-8, 2020, doi: 10.1051/e3sconf/202019506001.
- [17] Arrofiq, A. H., Afriani, L., & Iswan, I. (2016). Pengaruh variasi waktu pemeraman terhadap nilai uji kuat tekan bebas pada tanah lempung dan lanau yang distabilisasi menggunakan kapur pada kondisi optimum. *J. Rekayasa Sipil dan Desain*, vol. 4, no. 3, pp. 447-458.
- [18] Hardiyatmo, H. C. (1992). *Mekanika Tanah I*. Jakarta: PT. Gramedia Pustaka.

# Utilization of fly ash and bottom ash to increase the value of unconfined compression strength on subgrade

## ORIGINALITY REPORT

19%

SIMILARITY INDEX

14%

INTERNET SOURCES

12%

PUBLICATIONS

7%

STUDENT PAPERS

## PRIMARY SOURCES

- 1 Safitri Febriana, Priyadi Priyadi, Rianida Taisa. "PENGARUH APLIKASI ABU TERBANG BATUBARA DAN PUPUK KANDANG SEBAGAI BAHAN AMELIORAN TERHADAP PERTUMBUHAN TANAMAN KANGKUNG (*Ipomea reptans* Poir.)", Jurnal Agrotek Tropika, 2021  
Publication 1%
- 2 [garuda.kemdikbud.go.id](http://garuda.kemdikbud.go.id)  
Internet Source 1%
- 3 [nadre.ethernet.edu.et](http://nadre.ethernet.edu.et)  
Internet Source 1%
- 4 [rc.library.uta.edu](http://rc.library.uta.edu)  
Internet Source 1%
- 5 [transukma.uniba-bpn.ac.id](http://transukma.uniba-bpn.ac.id)  
Internet Source 1%
- 6 Muthia Anggraini, Virgo Trisep Haris, Alfian Saleh. "STABILISASI TANAH LEMPUNG DENGAN ABU TANDAN SAWIT DAN SEMEN 1%

# TERHADAP TINGKAT KEPADATAN TANAH",

Racic : Rab Construction Research, 2022

Publication

---

7	<a href="http://journals.itb.ac.id">journals.itb.ac.id</a> Internet Source	1 %
8	<a href="http://www.ijitee.org">www.ijitee.org</a> Internet Source	1 %
9	Dyah Lintang Trenggonowati, Achmad Bahauddin, Asep Ridwan, Yuyun Wulandari. "Proposed Action of Supply Chain Risk Mitigation Air Compressor Type L Unloading ¼ HP Using The Fuzzy – FMEA and Fuzzy – AHP Method in PT. XYZ", Journal of Innovation and Technology, 2021 Publication	1 %
10	B. V. Venkatarama Reddy. "Compressed Earth Block & Rammed Earth Structures", Springer Science and Business Media LLC, 2022 Publication	1 %
11	<a href="http://journal.eng.unila.ac.id">journal.eng.unila.ac.id</a> Internet Source	1 %
12	<a href="http://repository.umj.ac.id">repository.umj.ac.id</a> Internet Source	<1 %
13	<a href="http://jurnal.untirta.ac.id">jurnal.untirta.ac.id</a> Internet Source	<1 %
14	<a href="http://repository.its.ac.id">repository.its.ac.id</a> Internet Source	

---

<1 %

15

tangerangkab.go.id

Internet Source

<1 %

16

Submitted to Institute of Graduate Studies,  
UiTM

Student Paper

<1 %

17

Submitted to Curtin University of Technology

Student Paper

<1 %

18

S Subekti, R Bayuaji, M S Darmawan, N A  
Husin, B Wibowo, B Anugraha, S Irawan, D  
Dibiantara. "Review: Potential Strength of Fly  
Ash-Based Geopolymer Paste with  
Substitution of Local Waste Materials with  
High-Temperature Effect", IOP Conference  
Series: Materials Science and Engineering,  
2017

Publication

<1 %

19

Submitted to Universitas Sultan Ageng  
Tirtayasa

Student Paper

<1 %

20

Yilmaz, Yuksel, and Vehbi Ozaydin.  
"Compaction and shear strength  
characteristics of colemanite ore waste  
modified active belite cement stabilized high  
plasticity soils", Engineering Geology, 2013.

Publication

<1 %

- 
- 21 Submitted to Asian Institute of Technology <1 %  
Student Paper
- 
- 22 "12th International Conference on Structural Engineering and Construction Management", <1 %  
Springer Science and Business Media LLC, 2023  
Publication
- 
- 23 Submitted to Central Queensland University <1 %  
Student Paper
- 
- 24 Submitted to October University for Modern Sciences and Arts (MSA) <1 %  
Student Paper
- 
- 25 Tarek A. Kassim, Bernd R. T. Simoneit, <1 %  
Kenneth J. Williamson. "Chapter 2 Recycling Solid Wastes as Road Construction Materials: An Environmentally Sustainable Approach", Springer Science and Business Media LLC, 2005  
Publication
- 
- 26 Yoo, Yeong Seok, and Jun Ho Jo. <1 %  
"Characteristics of MSWI Ash and its Application to Zeolite Synthesis", Materials Science Forum, 2014.  
Publication
- 
- 27 doaj.org <1 %  
Internet Source
-

28	<a href="http://e-journal.uajy.ac.id">e-journal.uajy.ac.id</a> Internet Source	<1 %
29	<a href="http://semarakilmu.com.my">semarakilmu.com.my</a> Internet Source	<1 %
30	Submitted to Higher Education Commission Pakistan Student Paper	<1 %
31	<a href="http://moam.info">moam.info</a> Internet Source	<1 %
32	Submitted to Liverpool John Moores University Student Paper	<1 %
33	<a href="http://repository-ft.untirta.ac.id">repository-ft.untirta.ac.id</a> Internet Source	<1 %
34	<a href="http://garuda.ristekbrin.go.id">garuda.ristekbrin.go.id</a> Internet Source	<1 %
35	Lucia Rozumová, Oldřich Motyka, Kristína Čabanová, Jana Seidlerová. "Stabilization of waste bottom ash generated from hazardous waste incinerators", Journal of Environmental Chemical Engineering, 2015 Publication	<1 %
36	<a href="http://dspace.dtu.ac.in:8080">dspace.dtu.ac.in:8080</a> Internet Source	<1 %
37	<a href="http://etd.umi.ac.id">etd.umi.ac.id</a> Internet Source	<1 %

<1 %

38

Ahmed M. Al-Mahbashi, Muawia Dafalla.  
"Impact of placement and field conditions on hydraulic conductivity and lifetime of liners",  
Journal of King Saud University - Science, 2021

Publication

<1 %

39

Gunaydin, O.. "Prediction of artificial soil's unconfined compression strength test using statistical analyses and artificial neural networks", Advances in Engineering Software, 201009

Publication

<1 %

40

R Yanuari, D Septari, J A Rindy, M Olivia.  
"Geopolymer hybrid fly ash concrete for construction and conservation in peat environment: A review", IOP Conference Series: Earth and Environmental Science, 2021

Publication

<1 %

41

[dspace.lboro.ac.uk](https://dspace.lboro.ac.uk)

Internet Source

<1 %

42

[es.scribd.com](https://es.scribd.com)

Internet Source

<1 %

43

[etd.astu.edu.et](https://etd.astu.edu.et)

Internet Source

<1 %

44

[everant.org](https://everant.org)

Internet Source

<1 %

---

45 [www.mdpi.com](http://www.mdpi.com) <1 %  
Internet Source

---

46 [www.uc-bcf.edu.ph](http://www.uc-bcf.edu.ph) <1 %  
Internet Source

---

47 Kosson, D.S.. "An approach for estimation of contaminant release during utilization and disposal of municipal waste combustion residues", Journal of Hazardous Materials, 199605 <1 %  
Publication

---

48 [text-id.123dok.com](http://text-id.123dok.com) <1 %  
Internet Source

---

49 Ilknur Bozbey. "Effects of soil pulverization quality on lime stabilization of an expansive clay", Environmental Earth Sciences, 07/29/2009 <1 %  
Publication

---

50 Kamil Banaszekiewicz, Tadeusz Marcinkowski, Iwona Pasiecznik. "Fly Ash as an Ingredient in the Contaminated Soil Stabilization Process", Energies, 2022 <1 %  
Publication

---

---

Exclude quotes On

Exclude matches Off

Exclude bibliography On