

SYNTHESIS AND CHARACTERIZATION SUPERABSORBENT HYDROGELSO F PARTIALLY NEUTRALIZED ACRYLIC ACIDPREPARED USING GAMMA IRRADIATION; SWELLING AND THERMAL BEHAVIOR

Submission date: 04-Apr-2023 06:44PM (UTC+0700)
by Dhenia Ria Barleany

Submission ID: 2055562382

File name: 21197-40282-1-PB.pdf (416.81K)

Word count: 3260

Character count: 17183

11
**SYNTHESIS AND CHARACTERIZATION SUPERABSORBENT HYDROGELS
OF PARTIALLY NEUTRALIZED ACRYLIC ACID
PREPARED USING GAMMA IRRADIATION; SWELLING AND THERMAL BEHAVIOR**

Erizal^{1*}, Basril Abbas¹, Sulistioso Giat Sukaryo², and Dhena Ria Barleany³

¹Centre for Application of Isotopes and Radiation, Jl. Lebak Bulus Raya no. 49, Jakarta 12070, Indonesia

²Centre for Science and Technology of Advanced Materials, Jl. Raya Puspipstek, Tangsel-Banten, 15314, Indonesia

³Department of Chemical Engineering, Sultan Ageng Tirtayasa University
Jl. Jend. Sudirman KM.3, Cilegon-Banten 42435, Indonesia

24
Received March 17, 2015; Accepted August 19, 2015

ABSTRACT

A series of superabsorbent hydrogels were synthesized from partially neutralized acrylic acid with varying degree of neutralization (0-1) using gamma radiation. The effects of degree neutralization of acrylic acid on swelling ratio were studied. DSC measurement was performed to understand the type of end products resulting from irradiation. The morphologies of the hydrogels were examined using SEM. The chemical changes of the hydrogels were characterized using FTIR. At optimum conditions (10 kGy, 15 min), the hydrogels with neutralization degree 0.5 exhibited rapid swelling with the highest swelling ratio ~1000 g/g. The results of DSC studies confirmed the possible formation of the type hydrogels from irradiated partially neutralized acrylic acid, and the hydrogels showed large numbers of pores from SEM examination.

Keywords: hydrogel; superabsorbent; acrylic acid; irradiation; crosslinking

ABSTRAK

Satu seri hidrogel superabsorben asam akrilat yang dinetralkan sebagian dengan variasi derajat netralisasi (0-1) disintesis menggunakan iradiasi gamma. Pengaruh derajat netralisasi terhadap rasio swelling dipelajari. Pengukuran sifat termal hidrogel dilakukan menggunakan DSC untuk mengkonfirmasi jenis produk hasil iradiasi. Scanning elektron mikroskop dilakukan untuk menguji morfologi hidrogel. Perubahan kimia hidrogel diukur menggunakan FTIR. Pada kondisi optimum (10 kGy, 15 menit), hidrogel dengan derajat netralisasi 0,5 menunjukkan rasio swelling yang tinggi (~1000 g/g). Hasil pengujian DSC mengkonfirmasi jenis produk yang mungkin terbentuk dari hasil iradiasi asam akrilat yang dinetralkan sebagian, dan hasil pengujian SEM menunjukkan hidrogel berpori.

Kata Kunci: hidrogel; superabsorben; asam akrilat; iradiasi; ikatan silang

INTRODUCTION

Hydrogel superabsorbent (HSA) is a type of polymer-based ability to absorb some quantity of water. Each type of polymer HSA has different way of achieving superabsorbent behavior. HSA is essentially a cross-linked polymer which ability to absorb water hundreds of times of their dry weight, insoluble in water because of the 3-dimensional structure of the polymer network [1]. HSA is a very attractive material because of its solubility properties and a unique water transport capacity. When they absorbed water almost all parts of their network consists of water, they form is similar to the polymer caused by water. Due to the unique nature, the hydrogel HSA has a wide range of applications ranging from a urine absorbent material in baby diapers/women to drug delivery system. Furthermore, HSAs can also be used

for other purpose such as water storage containers for dry areas/agriculture [2], absorbing dyes and metal ions [3-4], a backup water source on horticulture crops [5-6], artificial snow [7], concentration of compounds evaporate [8], absorption of bacteria and fungi in wound dressings [9], elimination water body [10], and immobilization of urea [11].

Hydrogels of acrylic acid-base⁷ have been reported demonstrate special properties because of the presence of carboxylate acid as anion side groups in their network. When they are dissolved in water, the ionic hydrogels interaction with solvent/polymer, the polymer chains charges repeal each other, expands polymer coil and increase water uptake. To maintain the presence of anion groups of acrylic acid after polymerization can be done by neutralization of acid groups in the liquid phase (usually with sodium or

17
* Corresponding author. Tel/Fax : +62-21-7690709/7691607
Email address : erizal@batan.go.id

potassium hydroxide solution), and then followed with crosslinking for polymerization.

Polymerization of acrylic acid can be carried out by various methods including chemical and radiation induced crosslinking, respectively. The radiation technique seems to be superior to chemical crosslinking. The advantages of radiation technique application are easy process control, simultaneously hydrogel formation and sterilization in one step process, no need any initiators and crosslinkers ect. This makes irradiation, as one of the best choice for the preparation method of hydrogels [12]. However, some researchers have been reported on the radiation of acrylic acid aimed to prepare hydrogels [13]. Besides, the mechanisms poly(acrylic acid) radiolysis in water has been well studied. However, to now only limited information about swelling and characterization of hydrogels synthesized by radiation partially acrylic acid have been published [14-18]. The objective of this work was to investigate the swelling behavior of acrylic acid hydrogels partially neutralized from 0 up 1 neutralization degree (Dn) and its thermal behavior synthesized by using gamma radiation crosslinking in aqueous solution. The types of end products resulting from irradiation were examined using Differential Scanning Calorimetry (DSC). In addition, the chemical changes of hydrogels were measured using Fourier Transform Infra Red (FTIR) and the morphology of hydrogels were examined using Scanning Electron Microscope (SEM).

EXPERIMENTAL SECTION

Materials

Acrylic acid, in glacial form was purchased from Merck, Darmstadt Germany and was stored in a refrigerator before use. Potassium hydroxide (KOH) was obtained from Merck and used for neutralization. Potassium chloride (KCl), Sodium chloride (NaCl), Calcium chloride (CaCl₂) were also purchased from Merck. Distilled water was used in the polymerization and swelling experiments. All chemical were used as a received. All of the reagents were analytical grade used without purification.

Instrumentation

To confirm the crosslinking of the hydrogels was performed using Differential Scanning Calorimetry (DSC) Shimadzu, Japan. Approximately ± 5 mg samples for each measurement were heated from room temperature up to 600 °C with heating rate 10 °C/min. The surface morphology of hydrogels was studied by field emission scanning electron microscope (SEM), using JSM 6510 equipment (JEOL, Japan), with operating voltage of

30 kV. Samples of hydrogels were immersed in distilled water at room temperature until maximum swelling, then frozen at -80 °C and lyophilized. The freeze-dried hydrogel were fixed on brass holder and coated by sputtering with a thin Au layer in order to avoid charging effects. The chemical changes of hydrogels were measured using Fourier Transform Infra Red (FTIR) Shimadzu IR-Prestige-21 spectrometer model 800 series, Japan.

Procedure

Preparation of hydrogels

Crosslinked HSA were prepared using gamma γ - irradiation from cobalt -60 A series acrylic acid solution were prepared from 15 mL acrylic acid dissolved in 75 mL distilled water, and then partially neutralized with KOH solution at different neutralization degree of 0, 0.25, 0.50, 0.75 and 1. The mixtures were stirred with 200 rpm at room temperature until homogeneous, Then, the reaction mixtures were packed in polypropylene (PP) plastic bags, sealed and then irradiated at single dose of 5 kGy (dose rate 5 kGy/h) at room temperature in the irradiator Panorama, CAIR BATAN, Jakarta. The hydrogels were dried at 60 °C for 48 h, and milled up to 60-80 mesh.

Swelling measurements

Swelling ratio of HSA were determined gravimetrically. The dried HSA (W₀) in distilled water (or other solution), shake with 400 rpm rate at different time interval at room temperature. At predetermined time interval, the water containing the swollen HSA were filtered using stainless steel tea sieves (± 200 mesh) and the hydrogel was hanging for approximately 1 h until no more water drop off. The remaining volume of water was collected and measured as W_t. Swelling ratio of hydrogels calculated as follows;

$$\text{Swelling ratio} = W_t/W_0 \quad (1)$$

Where W₀ and W_t are the weights of dried hydrogel and swollen hydrogel at time t.

Equilibrium degree of swelling (EDS) hydrogels were determined using equation 1 and all the samples were measured triplicates.

RESULT AND DISCUSSION

The Main Mechanisms of Radiation-Induced Partially Acrylic Acid

The first a step of the reaction in this work was to partially neutralization of acrylic acid with varying concentration KOH solutions from 0 to 1 of neutralization degree, then exposure to gamma rays at a dose of 10 kGy, respectively. The radicals

polymerization reaction will be taken place in these solutions with the following the radiation mechanism stages such as initiation, propagation and termination [19]. In the initiation stage, radiolysis of water is occurred and resulted H and OH radicals. The radicals are recombined to produce H_2 and H_2O_2 gases. In addition, the H or OH radicals are attack the double bond of acrylic acid and potassium acrylic acid to produce their radicals, respectively. These radicals reaction are continued to the propagation stage, and finally produced a stable product, generally.

For acrylic acid monomer solution with $D_n = 0$, it meant that the solution containing mostly monomer acrylic acid. Thus, the final radiation products will be homopolymer of acrylic acid and the reaction can be illustrated Fig. 1.

For acrylic acid with $D_n = 1$, in which the acrylic acid anions predominate in solution and will be polymerized by radiation to its homopolymers of potassium acrylate salt in the final product, and the reaction can be illustrated as Fig. 2.

For acrylic acid with D_n 0.25, 0.50, and 9.75, in which the acrylic acid solution has been partially neutralized by KOH and resulted the solutions contain the mixture of acrylic acid molecules and its anions in the equilibrium state such as Fig. 3.

When these solutions are irradiated using gamma rays, the radiation polymerization reaction is occurred with following radiation mechanism reaction stages. Thus, the results of irradiation will be a crosslinked copolymer of acrylic acid and potassium acrylate and the reaction can be illustrated as Fig. 4.

Besides, the dissolved peroxides and homopolymers in minor amounts are present as irradiation side products.

DSC Characterization

Thermal behavior of the hydrogels was studied using DSC to confirm the type end products that might be produced from irradiating of acrylic acid partially neutralized and their thermogram are presented in Fig. 5 and decomposition temperatures (T_d) summarized in Table 1. Fig 5(a) shows the DSC scan of dried sample hydrogels with neutralization degree of 0. It is observed that the thermogram of dried hydrogel made from the resulting partially neutralized acrylic acid via gamma irradiation with $D_n = 0$, appeared with three glass transition peaks and a single sharp peak at T_d 461 °C in the exothermal process is shown in Fig. 5(a). In addition, Fig 5(b) shows the DSC scan of dried sample of acrylic acid hydrogel with neutralization degree of 1 ($D_n = 1$) appeared with a single broad decomposition temperature peak at 426.63 °C. Based on the characteristics of DSC thermogram peaks [20], it can be assumed that hydrogels with neutralization degree of 0 ($D_n = 0$) and 1 are presence in the crystalline and amorphous form of the dried hydrogels, respectively. The DSC curve of dried sample of acrylic acid hydrogels with neutralization degree of 0.25, 0.50, and 0.75 in Fig 5(b-d) shows two decomposition peaks, respectively. The first peak ranging from 340.40-358.75 °C and the second peak ranging from 385.0-450.45 °C.

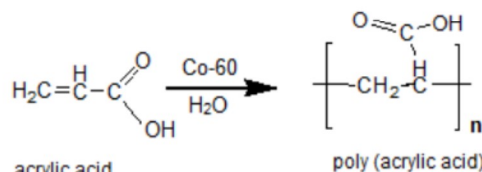


Fig 1. Radiation induced homopolymerization reaction of acrylic acid in aqueous solution

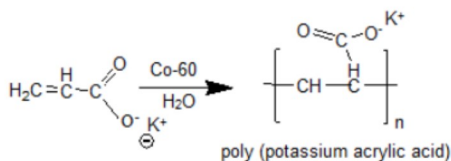


Fig 2. Radiation induced homopolymerization reaction of potassium acrylic acid in aqueous solution




Fig 3. Equilibrium state of acrylic acid monomer in aqueous solution

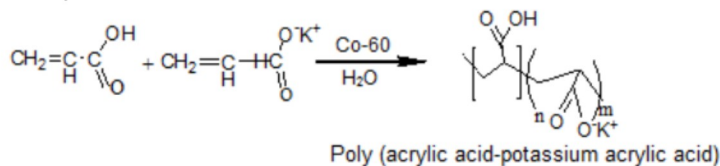


Fig 4. Radiation induced copolymerization reaction of potassium acrylic acid and acrylic acid in aqueous solution

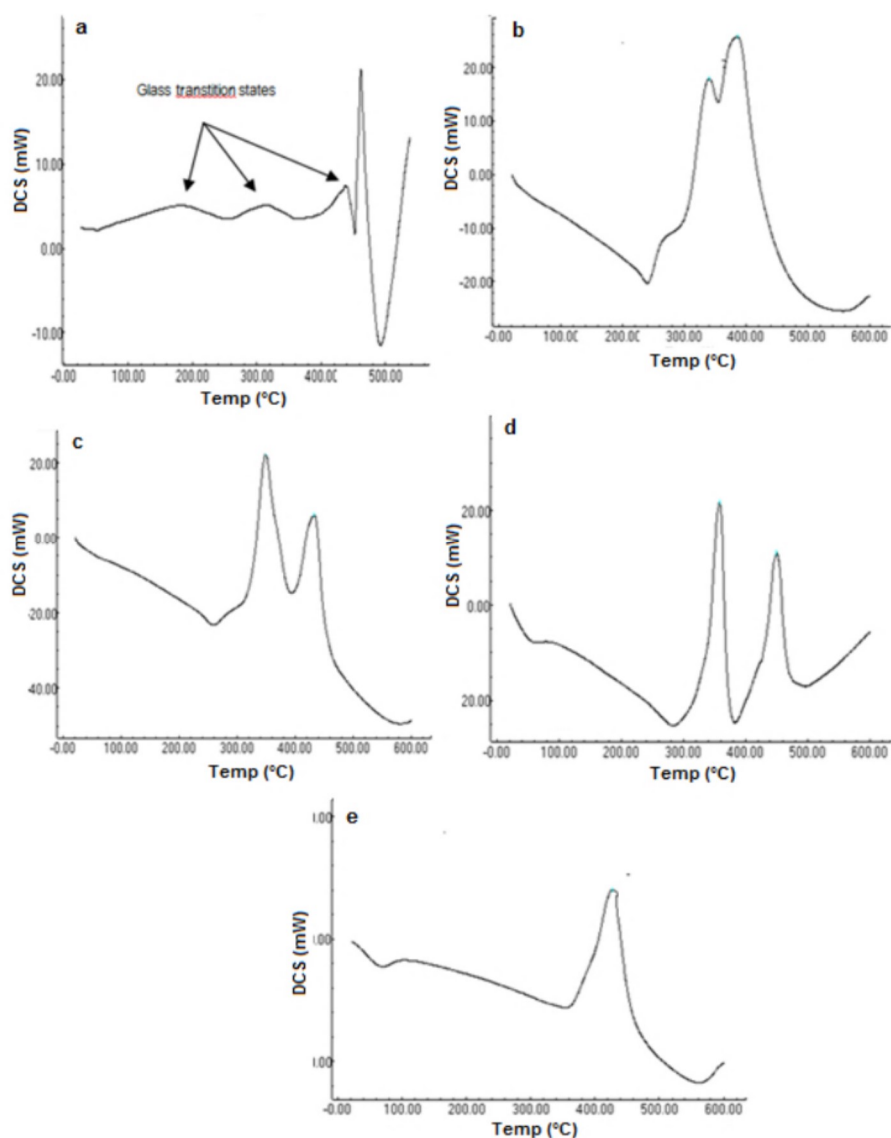


Fig 5. DSC thermogram of HSA of irradiated partially acrylic acid with varying Dn, (a) 0, (b) 0.25 , (c) 0.50, (d) 0.75, and (e) 1

A similar observation has been reported by Chapiro [21] and this has been analyzed that two peaks are presence as syndiotactic and atactic form of acrylic acid polymers.

SEM Photograph of HSA

1 The SEM photograph provides the pores geometry and size related to their specific location of the

hydrogels. Therefore, it gives relevant information the homogeneity and heterogeneity of the hydrogels network. For this purpose SEM pictures of hydrogel prepared from **1** 0.75 Dn with higher swelling ratio (~1000 g/g) were taken at the surface and interior of the hydrogels and **1** shown in Fig. 6. It can be seen that the hydrogel is covered by irregular pores with sizes ranging from 7.5–100 μm , and in some places covered

Table 1. Decomposition (Td) temperature of HSA acrylic acid based with different Dn prepared by gamma irradiation at a dose of 10 kGy

Sample(s) HSA of partially acrylic acid with Dn	Td ₁ (°C)	Td ₂ (°C)
0	461.51	-----
0.25	340.40	385.90
0.50	349.55	433.13
0.75	358.74	450.48
1.00	426.63	-----

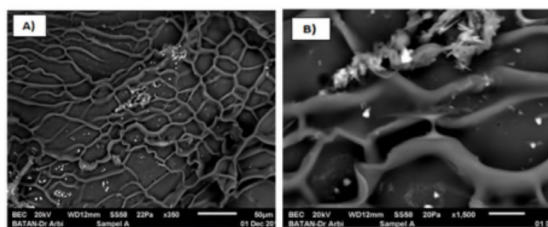


Fig 6. Scanning micrograph of the surface of HSA prepared from irradiated of 0.75 Dn of acrylic acid with swelling ratio ~1000g/g. The micrographs of the surface hydrogels were taken with a magnification, a) 350 x and b) 1500 x (the scale bar are 50 µm and 10 µm)

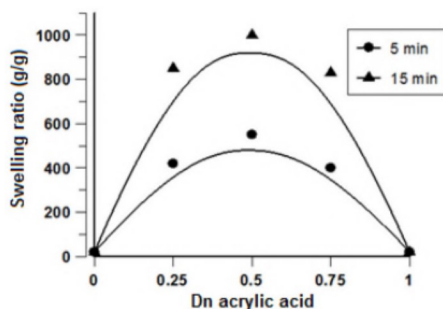


Fig 7. Swelling ratio of HSA in distilled water of irradiated partially neutralized acrylic acid with different Dn

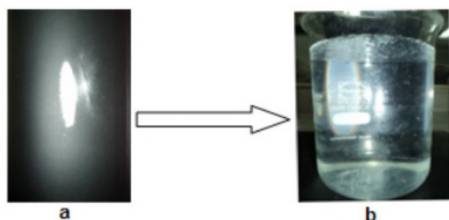


Fig 8. The swollen of HSA irradiated acrylic acid (Dn=0.5) in water with a high swelling capacity of 1000 g/g as super absorbent hydrogel a) Dried hydrogel (1g), b) swollen hydrogel in 1 L (1000 g) of water

by a thin skin of polymer. The presence of a polymeric skin has been describe for other hydrogel, and is probably related to the collapse of surface pores by a freeze drying process mainly in the hydrogels with large pores and thin walls.

Swelling Properties of Partially Neutralized Acrylic Acid Hydrogels

The effect of immersing time on swelling kinetics of partially neutralized acrylic acid hydrogels with the neutralization degree (Dn) in the range of 0–1 are presented in Fig. 7. It can be seen that as the neutralization degree of acrylic acid hydrogels increased, the equilibrium swelling ratio of hydrogels significantly decreased. While with increase immersing time from 5 min to 15 min, the swelling ratio of the hydrogels increased. The swelling ratios of hydrogels with neutralization degree of 0.25 and 0.75 was approximately 450 and 600 g/g, respectively and the optimum swelling ratio of hydrogel was reached 1000 g/g (shown in Fig. 7) from acrylic acid with Dn = 0.5. In contrast, for hydrogels with Dn = 0 and Dn = 1, the swelling ratio was low (~20 g/g). It is indicated that the prepared homopolymer acrylic acid hydrogels with D = 0 and D = 1.00 as a results of irradiation composed small amounts of crosslinking acrylic acid hydrogels which can absorb and retain small quantities of water. In addition for acrylic acid hydrogels with Dn in the range of 0.25–0.75 are composed of the mixtures of syndiotactic and atactic forms of acrylic acid hydrogels [21]. When they are dissolved in water, the carboxyl anions in the polymer backbone were exposed into water, the hydrogels rapidly swell due to the repulsive forces between carboxyl anions and the porosity sizes of the hydrogels increased with following water diffusion into the pores of hydrogels. Finally, the swelling ratio of the hydrogel increased significantly, and the optimum swelling ratio is obtained from hydrogel with Dn = 0.50 caused the highest possibility of repealing carboxylate anions in the hydrogel networks.

FTIR Characterization of HSA

The FTIR spectra of superabsorbent of partially neutralized acrylic acid with having 50% neutralization degree as a result gamma irradiation is presented in Fig. 9. It can be seen that at wave numbers of 3,700–3,000 cm^{-1} is a broad absorption band which corresponds to the stretching vibration of H groups, -CH stretching vibrations of the acrylate groups on the chain give absorption at 2,962 cm^{-1} . At the 1,674 range, is a peak corresponding to deformation vibrations of -C-OH, the peak at 1,570 cm^{-1}

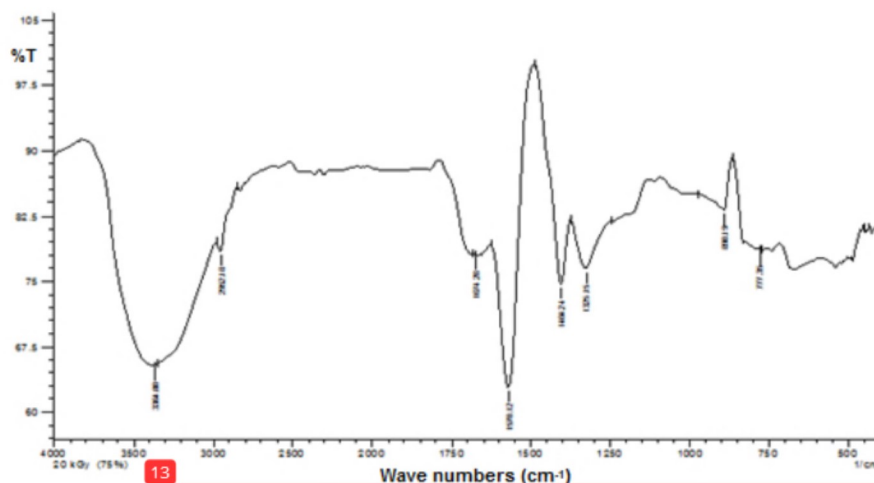


Fig 9. FTIR spectrum of superabsorbent hydrogels of partially neutralized acrylic acid prepared using gamma irradiation

is a peak corresponding to asymmetrical vibrations of -COO^- groups and the peak at $1,325\text{ cm}^{-1}$ is a peak of symmetrical vibrations of -COO^- . Based on this FTIR spectrum it can be proven that crosslinking of acrylic acid occurs at its double bond caused there is no double bond of acrylic acid appeared in the FTIR spectrum.

CONCLUSION

Superabsorbent hydrogels (HSA) with rapid swelling and a large capacity water absorption based on partially neutralized acrylic acid can be synthesized through gamma irradiation technique. The swelling behavior of HSA dependent on Dn of acrylic acid. The highest swelling capacity ($\sim 1000\text{ g/g}$) of HSA can be reached in 15 min of irradiated partially neutralized acrylic acid with having Dn = 0.50. The thermogram DSC confirmed possibilities of the type end products resulting from irradiated of partially neutralized acrylic acid. From SEM examination, the hydrogels had large numbers of pores. Spectra FTIR supported the role of double bond in radiation polymerization of acrylic acid.

ACKNOWLEDGEMENT

We wish for acknowledgement that the irradiation experiments were conducted at the Gamma Radiation Centre of Application Isotopes and Radiatio Jakarta, Indonesia. We wish to thanks Mr. Armanu for assistance in γ -irradiation of samples. We also wish to thank Prof. Zubaidah Irawati for her assistance in preparation of this manuscript.

REFERENCES

- Kabiri, K., Omidian, H., Zohuriaan-Mehr, M.J., and Doroudiani, S., 2010, *Polym. Compos.*, 32 (2), 277–289.
- Bucholz, F.L., and Graham, T., 1998, *Modern Superabsorbent Polymer Technology*, Wiley VCH, New York, 151.
- Li, S., 2010, *Bioresour. Technol.*, 101 (7), 2197–2202.
- Dhena, R.B., Sofiyati, Unayah, and Erizal, 2013, *J. Waste Manage. Technol.*, 16 (3), 62–73.
- Tomar, R.S., Gupta, I., Singhai, R., and Nagpal, A.K., 2007, *Des. Monomers Polym.*, 10 (1), 49–66.
- Nakason, C., Wohmang, T., Kaesaman, A., and Kiatkamjornwong, S., 2010, *Carbohydr. Polym.*, 81 (2), 348–357.
- Chang, C., Duan, B., Cai, J., and Zhang, L., 2010, *Eur. Polym. J.*, 46 (1), 92–100
- Flores, J.G., Herraiz, M., and Ruiz del Castillo, M.L., 2006, *J. Sep. Sci.*, 29 (17) 2677–2683
- Kamoun, E.A., Chen, X., Eldin, M.S.M., and Kenawy, E.S., 2015, *Arabian J. Chem.*, 8 (1), 1–14.
- Sannino, A., Demitri, C., and Madaghiele, M., 2009, *Materials*, 2 (2), 353–373.
- He, X.S., and Zhang, F.D., 2005, *Plant Nutr. Fert. Sci.*, 11 (3), 334–339.
- Erizal, Tjahyono, Dian, P.P., and Darmawan, 2013, *Indones. J. Chem.*, 13 (3), 41–46.
- Sheik, N., Jalili, L., and Anvari, F., 2010, *Radiat. Phys. Chem.*, 79 (6), 735–739.

14. Kostić, A., Adnadjević, B., Popović, A., and Jovanović, J., 2007, *J. Serb. Chem. Soc.*, 72 (11), 1139–1153.
15. Adnadjević, B., and Jovanović, J., 2008, *J. Appl. Polym. Sci.*, 107 (6), 3579–3587.
16. Hussain, Y.A., Liu, T., and Roberts, G.W., 2012, *Ind. Eng. Chem. Res.*, 51 (35), 11401–11408.
17. Ahmed, E.M., 2015, *J. Adv. Res.*, 6 (2), 103–121.
18. Wang, Y., Shi, X., Wang, W., and Wang, A., 2013, *Turk. J. Chem.*, 37, 149–159.
19. Caputo, G., Galia, F., Scrò, F., Spadaro, G., and Filardo, G., 2002, *Radiat. Phys. Chem.*, 63 (1), 45–51.
20. Colette, F.Q., 2011, *Water LLC*, TA Instrument, 1–11.
21. Chapiro, A., 1962, *Radiation Chemistry of Polymeric System*, Interscience, New York, 77–80.

SYNTHESIS AND CHARACTERIZATION SUPERABSORBENT HYDROGELS OF PARTIALLY NEUTRALIZED ACRYLIC ACID PREPARED USING GAMMA IRRADIATION; SWELLING AND THERMAL BEHAVIOR

ORIGINALITY REPORT

17%

SIMILARITY INDEX

5%

INTERNET SOURCES

14%

PUBLICATIONS

3%

STUDENT PAPERS

PRIMARY SOURCES

1	hdl.handle.net Internet Source	2%
2	Sheikh, N.. "A study on the swelling behavior of poly(acrylic acid) hydrogels obtained by electron beam crosslinking", Radiation Physics and Chemistry, 201006 Publication	2%
3	Esmail Jabbari, Samyra Nozari. "Swelling behavior of acrylic acid hydrogels prepared by γ -radiation crosslinking of polyacrylic acid in aqueous solution", European Polymer Journal, 2000 Publication	1%
4	Submitted to Universitas Diponegoro Student Paper	1%
5	www.mdpi.com Internet Source	1%

6	Markus Frank. "Superabsorbents", Wiley, 2003 Publication	1 %
7	mientayvn.com Internet Source	1 %
8	David Leal, Wim De Borggraeve, Maria V. Encinas, Betty Matsuhira, Robert Müller. "Preparation and characterization of hydrogels based on homopolymeric fractions of sodium alginate and PNIPAAm", Carbohydrate Polymers, 2013 Publication	1 %
9	Yaoyao Luo, Jingjing Li, Yichen Hu, Fei Gao, George Pak-Heng Leung, Funeng Geng, Chaomei Fu, Jinming Zhang. "Injectable thermo-responsive nano-hydrogel loading triptolide for the anti-breast cancer enhancement via localized treatment based on "two strikes" effects", Acta Pharmaceutica Sinica B, 2020 Publication	1 %
10	Submitted to University of Warwick Student Paper	1 %
11	Submitted to Universitas Sultan Ageng Tirtayasa Student Paper	1 %
12	Wenbo Wang. "Syntheses and properties of superabsorbent composites based on natural	1 %

guar gum and attapulгите", Polymers for
Advanced Technologies, 12/2008

Publication

13

Amol Tarachand Naikwadi, Bhuwanesh Kumar Sharma, Keyur D. Bhatt, Prakash A. Mahanwar. "Gamma Radiation Processed Polymeric Materials for High Performance Applications: A Review", Frontiers in Chemistry, 2022

Publication

1 %

14

Xiaoning Shi. "Enhanced swelling properties of a novel sodium alginate-based superabsorbent composites: NaAlg-g-poly(NaA-co-St)/APT", Journal of Applied Polymer Science, 08/05/2012

Publication

1 %

15

Lucas Barboza Moreira Pinheiro, Songsheng Tao, Elizabeth Culbertson, Gabriel Lima Barros de Araujo et al. "Evaluation of the polymorphic forms of ritonavir and lopinavir in raw materials and co-milled systems", International Journal of Pharmaceutics, 2022

Publication

<1 %

16

Santiago, F.. "Preparation of composites and nanocomposites based on bentonite and poly(sodium acrylate). Effect of amount of bentonite on the swelling behaviour", European Polymer Journal, 200701

Publication

<1 %

17 adoc.pub <1 %
Internet Source

18 Kacarevic-Popovic, Z.. "Radiolytic synthesis of Ag-poly(BIS-co-HEMA-co-IA) nanocomposites", Radiation Physics and Chemistry, 200708 <1 %
Publication

19 Rajive Singh Tomar, Indu Gupta, Reena Singhal, A. K. Nagpal. "Synthesis of Poly (Acrylamide-co-Acrylic Acid) based Superabsorbent Hydrogels: Study of Network Parameters and Swelling Behaviour", Polymer-Plastics Technology and Engineering, 2007 <1 %
Publication

20 Zhai Maolin, Li Jun, Yi Min, Ha Hongfei. "The swelling behavior of radiation prepared semi-interpenetrating polymer networks composed of polyNIPAAm and hydrophilic polymers", Radiation Physics and Chemistry, 2000 <1 %
Publication

21 www.researchgate.net <1 %
Internet Source

22 Yeşim Menceloğlu, Yusuf Ziya Menceloğlu, Senem Avaz Seven. "Triblock Superabsorbent Polymer Nanocomposites with Enhanced Water Retention Capacities and Rheological Characteristics", ACS Omega, 2022 <1 %

23

eproceeding.itp.ac.id

Internet Source

<1 %

24

www.birpublications.org

Internet Source

<1 %

25

Enade Perdana Istyastono, Muhammad Radifar, Nunung Yuniarti, Vivitri Dewi Prasasty, Sudi Mungkasi. "PyPLIF HIPPOS: A Molecular Interaction Fingerprinting Tool for Docking Results of AutoDock Vina and PLANTS", Journal of Chemical Information and Modeling, 2020

Publication

<1 %

Exclude quotes On

Exclude matches Off

Exclude bibliography On