

# Controlled Release of Metformin Hydrogen Chloride from Stimuli-responsive Hydrogel based on Poly(N- Isopropylacrylamide)/Chitosan/ Polyvinyl Alcohol Composite

*by Dhena Ria Barleany*

---

**Submission date:** 04-Apr-2023 06:56PM (UTC+0700)

**Submission ID:** 2055568051

**File name:** 31.\_Controlled\_Release...Jurnal\_Internasional\_Q2,\_IJTech.pdf (917.03K)

**Word count:** 5091

**Character count:** 27144



## Controlled Release of Metformin Hydrogen Chloride from Stimuli-responsive Hydrogel based on Poly(N- Isopropylacrylamide)/Chitosan/Polyvinyl Alcohol Composite

Dhena Ria Barleany<sup>1\*</sup>, Claudia Vivi Ananta<sup>1</sup>, Fistia Maulina<sup>1</sup>, Agus Rochmat<sup>1</sup>, Hafid Alwan<sup>1</sup>, Erizal<sup>2</sup>

<sup>1</sup>Departement of Chemical Engineering, Faculty of Engineering, University of Sultan Ageng Tirtayasa, Jl. Jend. Sudirman Km. 03, Cilegon, Banten 42435, Indonesia

<sup>2</sup>Centre for Application of Isotopes and Radiation, South Jakarta 7002, Indonesia

**Abstract.** Hydrogels are ideal biomaterials owing to their unique network structure that facilitates considerable hydrophilicity and biocompatibility. At the same time, hydrogels also possess soft physical properties when combined with living tissue. In this study, metformin hydrogen chloride (metformin HCl)-loaded stimuli-responsive poly(N-isopropylacrylamide) (pNIPAAm) –chitosan–polyvinyl alcohol (PVA) hydrogels were synthesized through a freezing and thawing procedure and subsequently subjected to gamma irradiation at room temperature. The gel content and the water absorption capacity of the synthesized hydrogels were analyzed. The polymer interaction in the matrix was observed by Fourier transform infrared spectroscopy, and the release of metformin HCl was studied in different pHs and temperatures. The hydrogels had 85% of the gel content and 373% of the water absorption capacity after 24 h of water immersion. The metformin HCl-loaded (pNIPAAm–chitosan–PVA) hydrogels demonstrated a sustained drug release profile over 7 h. The drug release exhibited pH-dependent and temperature-dependent behavior. The developed hydrogels showed good metformin HCl release ability at pH 3 and pH 6.86 at the temperature of 37°C. The results showed that pNIPAAm–chitosan–PVA hydrogels could be employed for controlled drug release of metformin HCl.

**Keywords:** Controlled drug release; Hydrogel; Metformin HCl

### 1. Introduction

Diabetes mellitus is a disorder that can cause morbidity and mortality. It is considered a serious disease in countries across the world. It can increase susceptibility to infections and reduce life expectancy (Chacko, 2016). Metformin hydrogen chloride (metformin HCl) is one of the most commonly used drugs to manage some forms of diabetes mellitus. It acts as an antihyperglycemic agent for the treatment of insulin-resistant diabetes mellitus (Zhou et al., 2018). Metformin release kinetics have been reported to have slow and incomplete absorption (bioavailability 50%–60%); approximately 30% to 50% of an oral dose is excreted unchanged in urine within 24 h, and about 30% is excreted in feces (Patiño-Herrera et al., 2019). Some of the symptoms that are often reported as the side effects of metformin HCl in the treatment of diabetes are mostly related to the gastrointestinal digestive tract, such as diarrhea, nausea, dyspepsia, flatulence, and abdominal pain

\*Corresponding author's email: [ria.barleany@untirta.ac.id](mailto:ria.barleany@untirta.ac.id), Tel.: +62-81318847532  
doi: 10.14716/ijtech.v11i3.2330

(Zhou et al., 2018). To increase adherence and reduce the side effects, metformin formulations in a controlled drug system have been developed (Patiño-Herrera et al., 2019; Shariatinia and Zahraee, 2017).

Drug delivery systems can increase the therapeutic effect of the drug at the target site by protecting the drug under physiological conditions, controlling its release, increasing or reducing its systemic circulation, and helping it reach the site of action (Khors et al., 2019). For these purposes, drugs are encapsulated in responsive materials that release their drug payloads under varying external triggers, such as pH, temperature, enzymes, reduction, diol moieties, reactive oxygen species, shear stress, ionic strength, and light (Fu et al., 2018).

Natural polymers are potential candidates to form hydrogels for drug delivery applications because of their biodegradability, high biocompatibility, and low toxicity. Among natural polymers, chitosan has recently attracted growing consideration (Usman et al., 2018) owing to its cationic nature and the presence of primary amino groups in its structure, which are responsible for its many useful properties. It also possesses pH- and temperature-responsive properties. These responsive properties of chitosan have led to it becoming an advanced biopolymer in the development of smart polymeric systems for delivery of numerous drugs (Muharam et al., 2015; Hasnain and Nayak, 2018; Krisanti et al., 2019). Chitosan can be modified with other substances to broaden the scope of its role as a drug carrier (Kusrini et al., 2014; Shariatinia and Zahraee, 2017).

Chitosan is a unique cationic polysaccharide that can be easily functionalized into different derivatives through chemical, radiation, and enzymatic procedures (Mittal et al., 2018). Chitosan can be used as a protective material for active substances (Usman et al., 2018). An emerging technique to improve its performance and expand its potential applications uses chemical modification to graft it to a vinyl monomer(s) and then cross-link the material. For enhancing chitosan's performance, one of the more intensively studied monomers is poly(N-isopropylacrylamide) (pNIPAAm) (Zhang et al., 2009; Carreira et al., 2010; Rasib et al., 2018). pNIPAAm is one of the most studied thermally-sensitive (thermo-responsive) polymers. It has a low critical solution temperature (LCST) of 32°C, which is a useful temperature for biomedical applications since it is close to body temperature (Carreira et al., 2010). Grafting pNIPAAm onto chitosan enables an increase in the water content of the graft following exposure to aqueous media along with improved mechanical and temperature-responsive properties (Zhang et al., 2009).

Polyvinyl alcohol (PVA) is a water-soluble synthetic polymer that has several desirable physical properties, such as elasticity and high hydrophilicity. It is cheap, non-toxic, and non-carcinogenic. It has good biocompatibility and high degree of swelling in aqueous solutions, which make it suitable for blending with chitosan in order to produce biodegradable blend hydrogels for controlled drug release systems (Abdel-Mohsen et al., 2011).

In this article, we report a model drug delivery system for the release of metformin HCl based on cross-linked PVA-chitosan blended hydrogels and pNIPAAm. We used metformin HCl as the drug because it is a type 2 diabetes drug that needs a controlled delivery system to ensure that the release occurs at the target site. The hydrogels were prepared through a procedure that combined physical freezing-thawing and gamma-ray irradiation. The release behaviors of metformin HCl from the hydrogel matrix at various pHs and temperatures were investigated. The use of the freezing-thawing method followed by gamma irradiation produced hydrogels with good mechanical properties, compact network structures, high porosity, and high absorption capacity without any hazardous initiators or cross-linking agents (Hamedi et al., 2018).

## 2. Methods

This research was carried out in several stages, namely the preparation of raw materials, synthesis of hydrogels, product analysis, and drug release tests using metformin as a model drug. The hydrogel synthesis stage involved freezing and thawing followed by gamma irradiation at a total dose of 20 kGy. The hydrogel products were then tested for the release of metformin HCl with varying pHs and temperatures of the media. Several predictions and hypotheses arise from our study. The first prediction is that pNIPAAm-chitosan-PVA hydrogels with high gel fraction and swelling capacity can be produced. The second prediction is that the release of metformin HCl from the hydrogel matrix will be affected by the pH and temperature of the media. This pH- and temperature-dependent rate of release of metformin HCl will be important for its application in oral therapy for the treatment of type 2 diabetes.

### 2.1. Materials

We obtained pharmaceutical grade chitosan with deacetylation degree of 85% (PT. Biotech Surindo, Cirebon, West Java, Indonesia), metformin HCl (DSM Anti-Infectives India Limited, India), pNIPAAm (PT. Merck Indonesia Tbk, Jakarta, Indonesia), and PVA (PT. Merck Indonesia Tbk, Jakarta, Indonesia). For the release study of metformin HCl, buffer solutions were used (pHs 3, 6.86, and 9). Distilled water was used throughout the experiment.

### 2.2. Hydrogel Preparation

1 g of chitosan was placed into a 250 mL glass beaker. Then, 12 mL of 1% (v/v) aqueous acetic acid solution was poured into the beaker and followed with continuous stirring to obtain homogenous 2% (w/v) chitosan solution. In a separate container, 10 g of PVA powder was placed into a 100 mL covered bottle. Then, 100 mL of distilled water was added to obtain 10% (w/v) of PVA solution. The bottle was placed in an autoclave and heated at 121°C for 20 min. Then, the bottle was removed from the autoclave and allowed to reach room temperature. In a 100 mL glass beaker glass, 2.5 g of pNIPAAm was placed, and 50 mL of chitosan solution was added followed by continuous stirring to obtain 5% (w/v) pNIPAAm solution. The solution mixture was homogenized by using a stirrer under room conditions. A total of 3 mL of the solution mixtures was introduced into vials of 3 mL capacity (20 mm and 30 mm in diameter). The next step was freezing and thawing, which was conducted by putting the solution mixture in a freezer for 16 h and then putting it out at room temperature for 8 h for one cycle. Next, it was subjected to gamma-ray irradiation in an irradiator at room temperature for 4 h to reach 20 kGy total dose (constant radiation rate of 5 kGy/h). A similar method was performed for the experiment of loading metformin HCl 30 mg in the hydrogel material. The hydrogel resulting from the irradiation process was removed from the bottle and characterized. The release behavior of metformin HCl from the hydrogel matrix at various pHs and temperatures was investigated.

### 2.3. Determination of Metformin HCl Maximum Absorption Wavelength

Ten mg of metformin HCl was dissolved into 500 mL distilled water. Then, 5 mL of the solution was pipetted and put in a cuvette to check its absorbance at a wavelength of 200-400 nm.

### 2.4. Metformin HCl Release Study

The drug-containing hydrogel was immersed in 100 mL buffer solution of pHs 3, 6.86, and 9 at the temperatures of 35°C, 37°C, and 40°C, and then, they were together placed into an incubator shaker tool with 10 rpm speed. The concentration of metformin HCl released from the hydrogel was observed for 1-7 h. At each one-hour interval, 10 mL of the solution

sample was pipetted. Distilled water was then added to the pH buffer solution at the same volume as the previous volume. Then, the materials were again placed back into the incubator shaker. The concentration was measured by UV-VIS spectrophotometry at maximum absorption wavelength.

### 2.5. Gel Fraction Analysis

The hydrogels of size 1×1 cm resulting from 20 kGy of irradiation were dried in an oven at 60°C to constant weight and then weighed ( $W_0$ ). Dried hydrogels were then immersed in distilled water for 24 h to remove the unreacted pNIPAAm-PVA-chitosan. The hydrogels were then wiped with filter paper and weighed ( $W_1$ ). The gel fraction was calculated according to the following equation:

$$\text{Gel fraction (\%)} = \frac{W_1}{W_0} \times 100 \%, \quad (1)$$

where  $W_1$  is the hydrogel weight after immersing (g), and  $W_0$  is the hydrogel weight before immersing (g).

### 2.6. Water Absorption Analysis

The hydrogel samples of size 1×1 cm obtained after the irradiation process were dried at 60°C in the oven and weighed ( $W_a$ ) and then immersed in distilled water at room temperature. Hydrogels were taken every hour, dried with filter paper, and then weighed ( $W_b$ ). The same treatment was performed each hour until 24 h. The swelling capacity of the hydrogel was determined by the following equation:

$$\text{Swelling capacity (\%)} = \frac{W_b - W_a}{W_a} \times 100\%, \quad (2)$$

where  $W_a$  is the hydrogel weight in dry condition (g), and  $W_b$  is the hydrogel weight in wet condition (g).

### 2.7. Cumulative Drug Release Percentage

The percentage of cumulative drug release from the hydrogel was calculated by the following formulas:

$$\text{Initial mass of sample} = \left( \frac{A-a}{b} \right) : 1000 \quad (3)$$

$$\text{Mass at initial volume} = \text{Initial mass of sample} \times \text{Initial volume} \quad (4)$$

$$\text{Drug release (\%)} = \frac{\text{mass at initial volume}}{\text{mass of drug}} \times 100\%, \quad (5)$$

where  $A$  is the percentage of absorbance,  $a$  is the intercept, and  $b$  is the slope.

$$\text{Cumulative drug release (\%)} = \text{Drug release in } t_{n-1}(\%) + \text{Drug release in } t_n(\%) \quad (6)$$

where  $t_{n-1}$  is the previous time, and  $t_n$  is the next hour

### 2.8. Fourier Transform Infrared Analysis (FTIR)

The hydrogel was crushed and mixed with fine powder of dried potassium bromide and then tested by using a Shimadzu Prestige 21 FTIR Spectrophotometer (Shimadzu Corp, Kyoto, Japan).

## 3. Results and Discussion

The reactant mixture containing pNIPAAm, PVA, and chitosan in liquid form was transformed into a gel after the irradiation process. The change in the shape of the material mixture before and after irradiation is shown in Figure 1.




**Figure 1** Change in the material's shape during the preparation: (a) Before irradiation; (b) Hydrogels of (pNIPAAm-chitosan-PVA) that have been cut after irradiation

The combination of chitosan with synthetic or other natural polymers forms semi-interpenetrating networks (IPNs). The mechanism of IPN and semi-IPN formation has been explained (Carreira et al., 2010). Based on the literature, it can be predicted that in the process of freezing-thawing and irradiation of pNIPAAm-chitosan-PVA polymer mixture, the radiation-sensitive PVA will form cross bonds first, and the easily degraded pNIPAAm and chitosan will enter into (penetration) the structure of the PVA network. According to Afshari et al. (2020), the freezing-thawing process can also cause physical cross bonds in the PVA solution. The combination of the freezing-thawing method with irradiation produces hydrogels with better mechanical properties compared with those samples prepared by irradiation.

### 3.1. FTIR Analysis

The functional group of the hydrogel product was compared to the raw materials (chitosan, pNIPAAm, and PVA) using an FTIR spectrophotometer. The FTIR spectra of chitosan powder, pNIPAAm, PVA, and the hydrogel product are presented in Figure 2.

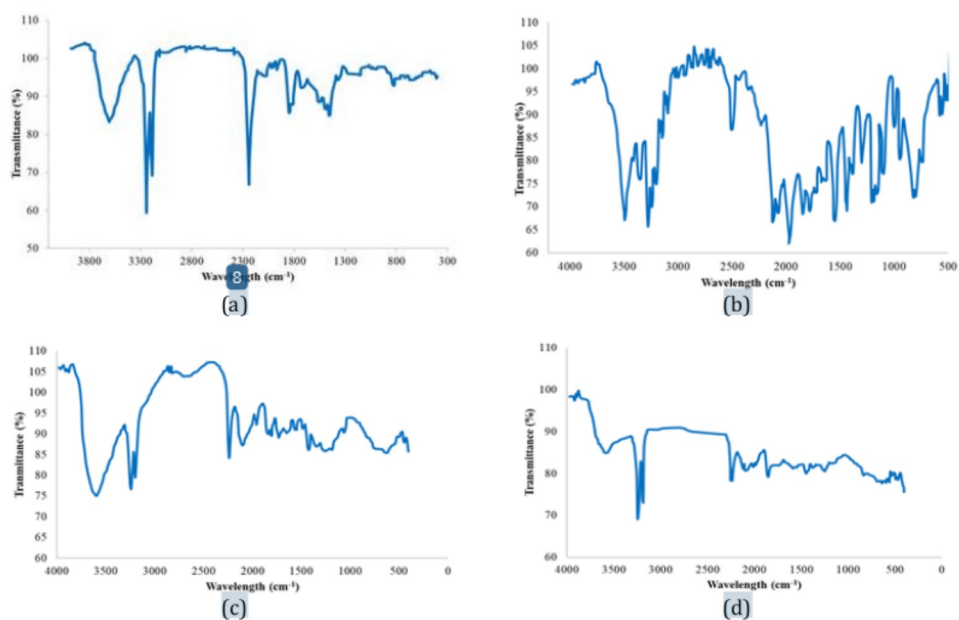


**Figure 2** FTIR spectra: (a) PVA; (b) pNIPAAm; (c) Chitosan; and (d) pNIPAAm-Chitosan-PVA hydrogel

In Figure 2a, it can be seen that the OH group of the PVA has a wide absorption peak at the wavelength of  $3621\text{ cm}^{-1}$  from the intramolecular and intermolecular hydrogen bonds; the CH groups are observed at wavelengths  $3241$  and  $3185\text{ cm}^{-1}$ , each associated with symmetrical stretching vibrations and the asymmetry of C-H alkyl groups; and the C=O group is observed at the wavelength of  $1850\text{ cm}^{-1}$  (Awada and Daneault, 2015). In Figure 2b, for pNIPAAm, it seems that the NH group vibration appears at the wavelength of  $3492\text{ cm}^{-1}$ , the stretching vibration of the  $\text{-C=C}$  appears at wavelengths of  $1560$  and  $1436\text{ cm}^{-1}$ , the strain CH is verified at  $3276\text{ cm}^{-1}$ , the CH vibration occurs at the wavelength of  $1380\text{ cm}^{-1}$ , the stretching vibration of the carbonyl C=O appears at the wavelength of  $1788\text{ cm}^{-1}$ , and the CN group is observed at the wavelength of  $1097\text{ cm}^{-1}$  (Seddiki and Aliouche, 2013; Wang et al., 2015). Figure 2c shows the chitosan functional groups, where the OH and NH functional groups have strong absorption peaks at the wavelength of  $3423.65\text{ cm}^{-1}$ , the symmetrical stretching adsorption and CH asymmetry group appear at wavelengths of  $3240\text{ cm}^{-1}$  and  $3196\text{ cm}^{-1}$ , the N-acetyl group residues are confirmed at the wavelength of  $1673\text{ cm}^{-1}$  (the stretching pattern adsorbs C=O on amides) and the  $1435\text{ cm}^{-1}$  take (the CN strain on the amide group pattern), and the absorption band of  $1102\text{ cm}^{-1}$  can be suspected as the stretching asymmetry of the C-O-C group (Queiroz et al., 2015). The pNIPAAm-chitosan-PVA hydrogel spectrum is shown in Figure 2(d), which represents the combination of the peaks of the three ingredients. The OH and NH functional groups have absorption peaks at the wavelength of  $3609\text{ cm}^{-1}$ , the symmetry stretching adsorption and the CH asymmetry group appear at wavelengths of  $3247\text{ cm}^{-1}$  and  $3195\text{ cm}^{-1}$ , the C=O group is seen at the wavelength of  $1863\text{ cm}^{-1}$ , the CO group is observed at the wavelength of  $1174\text{ cm}^{-1}$ , and the CN group is seen at the wavelength of  $1278\text{ cm}^{-1}$ .

### 3.2. Gel Fraction and Water Absorption Analysis

In this study, hydrogel products were made three times with a constant dose of gamma-ray irradiation of dose  $20\text{ kGy}$ . The three products were then analyzed for their gel fraction and their ability to absorb water.

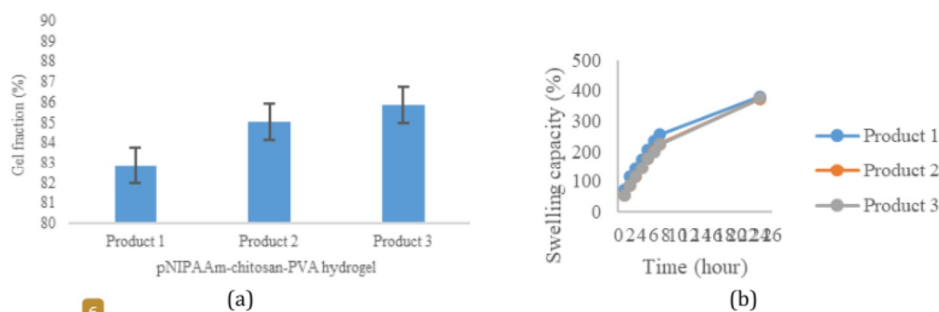

**Figure 3** Physical properties of the hydrogel product: (a) Gel fraction; (b) Swelling

Figure 3a shows the gel fraction values of three hydrogel products after identical irradiation. Product 1 has the gel fraction value of 82.88%, product 2 has the gel fraction value of 85.03%, and product 3 has the gel fraction value of 85.86%. The gel fraction indicates the number of cross-links that occur between the polymers in the hydrogel (Alcântara et al., 2012). The higher the density of cross-links formed, the lower the swelling capacity of the hydrogel. Therefore, the ability of water to enter and exit the hydrogel is reduced. In this way, the drug release process can be controlled. The relationship between

the swelling ability of the pNIPAAm–chitosan–PVA hydrogel and the immersion time is shown in Figure 3b.


The hydrogel has a cross-link that will form a three-dimensional macromolecular network with the ability to absorb water that is far beyond its own weight or volume (commonly referred to as superabsorbent material). The hydrogel is insoluble in water. In the mechanism of water absorption by hydrogels, the hydrophilic group of the polymer plays an important role. When the polymer is immersed in water, a reaction occurs with hydrogen atoms that releases positive ions. This results in negative charges along the repelling polymer chain, which forces the polymer chain to open and bind water with hydrogen bonds (Kalhapure et al., 2016). There is also an increase in the hydrogel porosity as water diffuses into the hydrogel pores (Erizal et al., 2015).

Hydrogels can generally absorb water that is more than 400 times their weight (Kalhapure et al., 2016). In this study, the water absorption value of the pNIPAAm–chitosan–PVA hydrogel was 373% (373 times its own dry weight).

### 3.3. Metformin HCl Release Study

The result of the maximum wavelength measurement for metformin HCl is shown in Figure 4a. Accordingly, the analysis of metformin HCl concentration release from the hydrogel matrix was carried out at the wavelength of 230 nm.

The metformin HCl release analysis was used to determine the cumulative amount of drug that was released from the hydrogel matrix. The results from the release of 30 mg of metformin HCl from the hydrogel at pHs 3, 6.86, and 9 at temperatures of 35°C, 37°C, and 40°C, respectively, are shown in Figures 4b, 4c, 4d. The metformin HCl drug release test was carried out for up to 7 h to conform to the standards of the U.S. Pharmacopeial Convention 2018 (The United States Pharmacopeial Convention, 2018), in which on average the release was carried out for 1 to 10 h to test the dissolution amount of metformin HCl tablets.

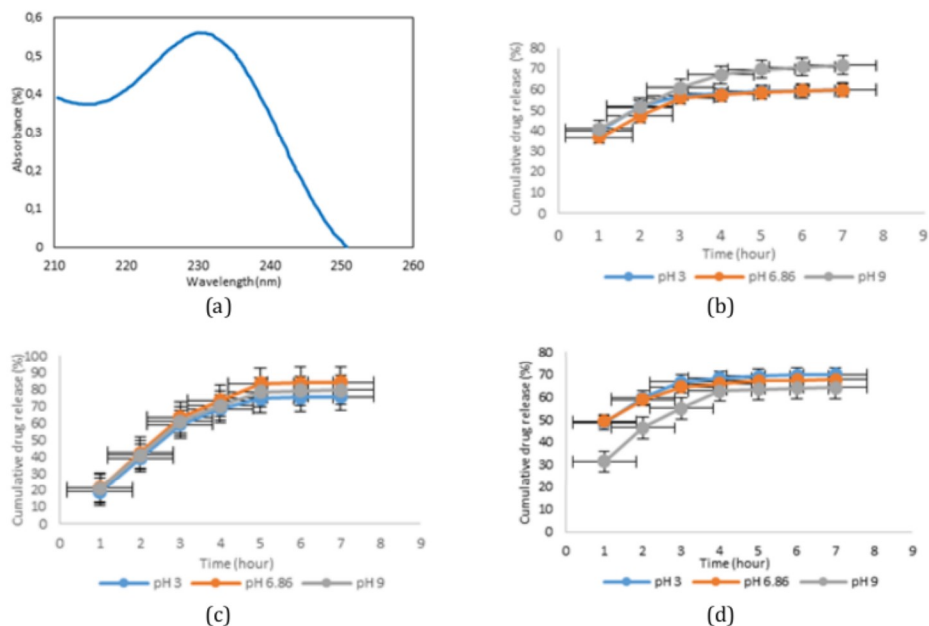

**Figure 4** Cumulative release of metformin HCl: (a) Maximum absorbance of metformin HCl using UV-Vis spectrophotometry. Relation between time and cumulative release of metformin HCl at different temperatures: (b) 35°C; (c) 37°C; and (d) 40°C



As can be seen in Figures 4b, 4c, and 4d, the release profiles of all conditions show that the cumulative release first increases with time and then becomes almost constant up to 7 h. This is an appropriate pattern for a controlled drug release, as it is a way to achieve a fixed plasma drug concentration at all times. The drug is delivered continuously at a predetermined rate for the long term (Kakar et al., 2014).

High release values of metformin HCl were found at 35°C (36–40%) at pH 6.86 and 40°C (31–49%) at pH 9 in the first hour. At 37°C, the release was in the range of 17–21% for all pH levels. This pattern is known as the burst effect, which is an uncontrolled release of the drug from the surface of the hydrogel because of the pH-responsive polymer particle size (Rizi et al., 2011). High release of the drug in the initial hours was also observed in an in vitro drug release study of metformin encapsulated in chitosan matrices (Ghazaie et al., 2017). The study reported that the metformin–chitosan composite without any additional coating released almost all of the drug in 37. Other studies found different burst release profiles and sustained release periods depending on several factors, including the composition of the composite material used as a drug carrier, the particle size, pH, and temperature.

### 3.3.1.27. Effect of temperature on drug release

Increase of temperature results in an increase of diffusion of drug molecules when immersed in an extracting medium (Lin et al., 2003). Consistent with this, it can be seen in Figures 4b, 4c, and 4d that there was an increase in the rates of metformin HCl release from the hydrogel at 37°C and 40°C relative to the rate at 35°C, especially at pH 3 and pH 6.86. As body temperature can change because of fever, local infection, or disease, this characteristic is advantageous for the design of controlled drug delivery systems (Carreira et al., 2010).

In the first two hours, the released metformin HCl ranged from 39%–60%; in the fourth hour, it ranged from 57%–74%; and at the sixth hour, it ranged from 59%–84%. The release behavior of metformin HCl from the hydrogel in this study shows that this system was temperature-responsive, and 37°C is the temperature that gives the best curve compared with the standard from USP Convention 2018.

### 3.3.1.22. Effect of pH on drug release

The pH in the gastrointestinal tract varies from ~1.5 to 4 in the stomach and ~7 to 8.5 in the small intestine (Shariatnia and Zahraee, 2017). For the oral administration of a drug intended for intestinal release, the coating material must hold the drug temporarily in the stomach (acidic pH) and release it once in the intestine (neutral pH) (Carreira et al., 2010).

In the three temperature variations studied, it appears that a temperature of 37°C provides a profile that is in line with expectations. At this temperature, the amount of metformin HCl released at acidic condition is lower than that at the pH of neutral and alkaline media. At pH 3, the hydrogel matrix releases 19.42% of the drug in the first hour, and the cumulative released amount reaches 75.67% in the seventh hour; at pH 6.86, the cumulative drug release is equal to 21.67% in the first hour and 84.27% in the seventh hour; and at pH 9, the cumulative drug release is 21.22% in the first hour and 79.35% in the seventh hour. This data shows that the pNIPAAm–chitosan–PVA hydrogel produced in this study is suitable for the release of metformin HCl under acidic (stomach) conditions, which is usually faster than neutral or alkaline (intestine) conditions.

## 4. Conclusions

From this study, it can be concluded that a pH- and temperature-responsive pNIPAAm–chitosan–PVA hydrogel can be synthesized through a combination of physical and chemical

crosslinking by freezing and thawing followed by gamma irradiation. A dose of 20 kGy gamma-ray irradiation can produce a hydrogel with a gel fraction of 85% and water absorption capacity of 373% after 24 h of immersion. The developed hydrogels showed good metformin HCl release ability at the temperature of 37°C. The results showed that pNIPAAm–chitosan–PVA hydrogel hydrogels could be employed for controlled drug release of metformin HCl.

### Acknowledgements

We highly appreciate the financial support from the University of Sultan Ageng Tirtayasa (UNTIRTA) through the “Competency Based Research Grant Program” for fiscal year 2018 (contract number: 667/UN43.9/PP/KT/2018).

### References

- Abdel-Mohsen, A.M., Aly, A.S., Hrdina, R., Montaser, A.S., Hebeish, A., 2011. Eco-synthesis of PVA/Chitosan Hydrogels for Biomedical Application. *Journal of Polymers and Environment*, Volume 19(4), pp. 1005–1012
- Afshari, M.J., Sheik, N., Afarideh, H., 2015. PVA/CM-chitosan/honey Hydrogels Prepared by using the Combined Technique of Irradiation Followed by Freezing-thawing. *Radiation Physics and Chemistry*, Volume 113, pp. 28–35
- Alcântara, M.T.S., Brant, A.J.C., Giannini, D.R., Pessoa, J.O.C.P., Andrade, A.B., Riella, H.G., Lugão, A.B., 2012. Influence of Dissolution Processing of PVA Blends on the Characteristics of their Hydrogels Synthesized by Radiation-Part I: Gel Fraction, Swelling, and Mechanical Properties. *Radiation Physics and Chemistry*, Volume 81(9), pp. 1465–1470
- Awada, H., Daneault, C., 2015. Chemical Modification of Poly(Vinyl Alcohol) in Water. *Applied Sciences*, Volume 5(4), pp. 840–850
- Carreira, A.S., Gonçalves, F.A.M.M., Mendonça, P.V., Gil, M.H., Coelho, J.F.J., 2010. Temperature and pH Responsive Polymers based on Chitosan: Applications and New Graft Copolymerization Strategies based on Living Radical Polymerization. *Carbohydrate Polymers*, Volume 80(3), pp. 618–630
- Chacko, E., 2016. Blunting Post-meal Glucose Surges in People with Diabetes. *World Journal Diabetes*, Volume 7(11), pp. 239–242
- Erizal, Abbas, B., Sukaryo, S.G., Barleany, D.R., 2015. Synthesis and Characterization Superabsorbent Hydrogels of Partially Neutralized Acrylic Acid Prepared using Gamma Irradiation: Swelling and Thermal Behavior. *Indonesian Journal of Chemistry*, Volume 15(3), pp. 281–287
- Fu, X., Hosta-Rigau, L., Chandrawati, R., Cui, J., 2018. Multi-Stimuli-Responsive Polymer Particles, Film, and Hydrogels for Drug Delivery. *Chem*, Volume 4(9), pp. 2084–2107
- Ghazaie, M., Ghiaci, P., Ghiaci, M. 2017. Study on Release of Naproxen and Metformin Encapsulated in Biopolymer-Inorganic Mesoporous Matrices as Controlled Drug-Delivery Systems. *Microporous and Mesoporous Materials*, Volume 244, pp. 291–300
- Hamed, H., Moradi, S., Hudson, S.M., Tonelli, A.E. 2018. Chitosan Based Hydrogels and Their Applications for Drug Delivery in Wound Dressings: A Review. *Carbohydrate Polymers*, Volume 199, pp. 445–460
- Hasnain, M.S., Nayak, A.K., 2018. Chitosan as Responsive Polymer for Drug Delivery Applications. *Stimuli Responsive Polymeric Nanocarriers for Drug Delivery Applications, Types and Triggers*, Volume 1, pp. 581–605

- Kakar, S., Singh, R., Semwal, A., 2014. Drug Release Characteristics of Dosage Form: A Review. *Journal of Coastal Life Medicine*, Volume 2(4), pp. 332–336
- Kalhpure, A., Kumar, R., Singh, V.P., Pandey, D.S., 2016. Hydrogels: A Boon for Increasing Agricultural Productivity in Water-Stressed Environment. *Current Science*, Volume 3(11), pp. 1773–1779
- Khors, N.J., Liyanage, T., Venkatesan, N., Najarzadeh, A., Puleo, D.A., 2019. Drug Delivery Systems and Controlled Release. *Reference Module in Biological Sciences: Encyclopedia of Biomedical Engineering*, pp. 316–329
- Krisanti, E.A., Hijrianti, N., Mulia, K., 2019. Preparation and Evaluation of Alginate-Chitosan Matrices Loaded with Red Ginger Oleoresin using the Ionotropic Gelation Method. *International Journal of Technology*, Volume 10(8), pp. 1513–1522
- Kusrini, E., Arbianti, R., Sofyan, N., Abdullah, M.A.A., Andriani, F., 2014. Modification of Chitosan by using Samarium for Potential use in Drug Delivery System. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, Volume 120, pp. 77–83
- Lin, D.M., Kalachandra, S., Valiyaparambil, J., Offenbacher S., 2003. A Polymeric Device for Delivery of Anti-Microbial and Anti-fungal Drugs in the Oral Environment: Effect of Temperature and Medium on the Rate of Drug Release. *Dental Materials*, Volume 19, pp. 589–596
- Mittal, H., Ray, S.S., Kaith, B.S., Bhatia, J.K., Sukriti, Sharma, J., Alhassan, S.M., 2018. Recent Progress in the Structural Modification of Chitosan for Applications in Diversified Biomedical Fields. *European Polymer Journal*, Volume 109, pp. 402–434
- Muharam, Y., Purwanto, W.W., Mulia, K., Wulan, P.P.D.K., Marzuki, I., Dewi, M.N., 2015. Mathematical Model Controlled Potassium Chloride Release Systems from Chitosan Microspheres. *International Journal of Technology*, Volume 6(7), pp. 1228–1237
- Patiño-Herrera, R., Louvier-Hernández, J.F., Escamilla-Silva, E.M., Chaumel, J., Escobedo, A.G.P., Pérez, E., 2019. Prolonged Release of Metformin by SiO<sub>2</sub> Nanoparticles Pellets for Type II Diabetes Control. *European Journal of Pharmaceutical Sciences*, Volume 131, pp. 1–8
- Queiroz, M.F., Melo, K.R.T., Sabry, D.A., Sasaki, G.L., Rocha, H.A.O., 2015. Does the Use of Chitosan Contribute to Oxalate Kidney Stone Formation?. *Marine Drugs*, Volume 13(1), pp. 141–158
- Rasib, S.Z.M., Ahmad, Z., Khan, A., Akil, H.M., Othman, M.B.H., Hamid, Z.A.A., Ullah, F., 2018. Synthesis and Evaluation on pH- and Temperature-responsive Chitosan-p(MAA-co-NIPAM) Hydrogels. *International Journal of Biological Macromolecules*, Volume 108, pp. 367–375
- Rizi, K., Green, R.J., Khutoryanskaya, O., Donaldson, M., Williams, A.C., 2011. Mechanism of Burst Release from pH-responsive Polymeric Microparticles. *Journal Pharmacy and Pharmacology*, Volume 63(9), pp. 1141–1155
- Seddiki, N., Aliouche, D., 2013. Synthesis, Rheological Behavior and Swelling Properties of Copolymer Hydrogels based on Poly(N-Isopropylacrylamide) with Hydrophilic Monomers. *Bulletin of the Chemical Society of Ethiopia*, Volume 27(3), pp. 447–457
- Shariatnia, Z., Zahraee, Z., 2017. Controlled Release of Metformin from Chitosan-based Nanocomposite Films Containing Mesoporous MCM-41 Nanoparticles as Novel Drug Delivery Systems. *Journal of Colloid and Interface Science*, Volume 501, pp. 60–76
- The United States Pharmacopeial Convention, 2018. Metformin Hydrochloride Extended-Release Tablets. *USP-NF Monograph (Revision Bulletin)*
- Usman, A., Kusrini, E., Widiatoro, A.B., Hardiya, E., Abdullah, N.A., Yulizar, Y., 2018. Fabrication of Chitosan Nanoparticles Containing Samarium Ion Potentially Applicable

- for Fluorescence Detection and Energy Transfer. *International Journal of Technology*, Volume 9(6), pp. 1112–1120
- Wang, L., Zhao, X., Zhang, Y., Zhang, W., Ren, T., Chen, Z., Wang, F., Yang, H., 2015. Fabrication of Intelligent Poly(N-Isopropylacrylamide)/Silver Nanoparticle Composite Films with Dynamic Surface-Enhanced Raman Scattering Effect. *RSC Advances*, Volume 5(50), pp. 40437–40443
- Zhang, H.F., Zhong, H., Zhang, L.L., Chen, S.B., Zhao, Y.J., Zhu, Y.L., 2009. Synthesis and Characterization of Thermosensitive Graft Copolymer of N-Isopropylacrylamide with Biodegradable Carboxymethylchitosan. *Carbohydrate Polymers*, Volume 77(4), pp. 785–790
- Zhou, T., Xu, X., Du, M., Zhao, T., Wang, J., 2018. A Preclinical Overview of Metformin for the Treatment of Type 2 Diabetes. *Biomedicine and Pharmacotherapy*, Volume 106, pp. 1227–1235

# Controlled Release of Metformin Hydrogen Chloride from Stimuli-responsive Hydrogel based on Poly(N-Isopropylacrylamide)/Chitosan/Polyvinyl Alcohol Composite

## ORIGINALITY REPORT

**21** %  
SIMILARITY INDEX

**9** %  
INTERNET SOURCES

**17** %  
PUBLICATIONS

**3** %  
STUDENT PAPERS

## PRIMARY SOURCES

**1** M. Saquib Hasnain, Amit Kumar Nayak. "Chitosan as responsive polymer for drug delivery applications", Elsevier BV, 2018 **1** %  
Publication

**2** [www.mdpi.com](http://www.mdpi.com) **1** %  
Internet Source

**3** A.S. Carreira, F.A.M.M. Gonçalves, P.V. Mendonça, M.H. Gil, J.F.J. Coelho. "Temperature and pH responsive polymers based on chitosan: Applications and new graft copolymerization strategies based on living radical polymerization", Carbohydrate Polymers, 2010 **1** %  
Publication

**4** Shiyu Zong, Hankang Wen, Hui Lv, Tong Li, Ruilin Tang, Liujun Liu, Jianxin Jiang, Shengpeng Wang, Jiufang Duan. "Intelligent hydrogel with both redox and thermo-response based on cellulose nanofiber for

# controlled drug delivery", Carbohydrate Polymers, 2021

Publication

---

5	<a href="#">dokumen.pub</a> Internet Source	1 %
6	<a href="#">worldwidescience.org</a> Internet Source	1 %
7	<a href="#">www.science.gov</a> Internet Source	1 %
8	Submitted to Universitas Sultan Ageng Tirtayasa Student Paper	1 %
9	Jittima Amie Luckanagul, Chutamart Pitakchatwong, Pahweenvaj Ratnatilaka Na Bhuket, Chawanphat Muangnoi et al. "Chitosan-based polymer hybrids for thermo- responsive nanogel delivery of curcumin", Carbohydrate Polymers, 2018 Publication	1 %
10	Tingting Zhou, Xin Xu, Mengfan Du, Tong Zhao, Jiaying Wang. "A preclinical overview of metformin for the treatment of type 2 diabetes", Biomedicine & Pharmacotherapy, 2018 Publication	1 %
11	Radian Radian, Budiyati Ichwan, Islah Hayat, Islah Hayat. "Nanotechnology for dryland	1 %

agriculture water saving: Biodegradable hydrogel application in sweet corn (*Zea mays saccharate* Sturt) productio", Emirates Journal of Food and Agriculture, 2022

Publication

---

12

M.D. Figueroa-Pizano, I. Vélaz, F.J. Peñas, P. Zavala-Rivera, A.J. Rosas-Durazo, A.D. Maldonado-Arce, M.E. Martínez-Barbosa. "Effect of freeze-thawing conditions for preparation of chitosan-poly (vinyl alcohol) hydrogels and drug release studies", Carbohydrate Polymers, 2018

Publication

---

1 %

13

Rosalba Patiño-Herrera, José Francisco Louvier-Hernández, Eleazar M. Escamilla-Silva, Julie Chaumel et al. "Prolonged release of metformin by SiO<sub>2</sub> nanoparticles pellets for type II diabetes control", European Journal of Pharmaceutical Sciences, 2019

Publication

---

1 %

14

Hemant Mittal, Suprakas Sinha Ray, Balbir Singh Kaith, Jaspreet Kaur Bhatia, Sukriti, Jitender Sharma, Saeed M. Alhassan. "Recent progress in the structural modification of chitosan for applications in diversified biomedical fields", European Polymer Journal, 2018

Publication

---

<1 %

15 Marieh Ghazaie, Payam Ghiaci, Mehran Ghiaci. "Study on release of naproxen and metformin encapsulated in biopolymer-inorganic mesoporous matrices as controlled drug-delivery systems", Microporous and Mesoporous Materials, 2017

Publication

<1 %

16 Zhao, Jin. "Chitosan-Based Gels for the Drug Delivery System", Chitosan-Based Hydrogels Functions and Applications, 2011.

Publication

<1 %

17 [link.springer.com](http://link.springer.com)

Internet Source

<1 %

18 Nawal Shaltout. "Effect of Electron Beam Irradiation and Ethylene Vinyl Acetate Copolymer on the Properties of NBR/HDPE Blends", Journal of Macromolecular Science Part A, 02/2010

Publication

<1 %

19 [www.ncbi.nlm.nih.gov](http://www.ncbi.nlm.nih.gov)

Internet Source

<1 %

20 M.J. Afshari, N. Sheikh, H. Afarideh. "PVA/CM-chitosan/honey hydrogels prepared by using the combined technique of irradiation followed by freeze-thawing", Radiation Physics and Chemistry, 2015

Publication

<1 %



21	"Fundamentals of Drug Delivery", Wiley, 2021 Publication	<1 %
22	Excipient Applications in Formulation Design and Drug Delivery, 2015. Publication	<1 %
23	Submitted to School of Business and Management ITB Student Paper	<1 %
24	Submitted to University of Greenwich Student Paper	<1 %
25	Submitted to VIT University Student Paper	<1 %
26	<a href="http://researchspace.csir.co.za">researchspace.csir.co.za</a> Internet Source	<1 %
27	D.M Lin, S Kalachandra, J Valiyaparambil, S Offenbacher. "A polymeric device for delivery of anti-microbial and anti-fungal drugs in the oral environment: effect of temperature and medium on the rate of drug release", Dental Materials, 2003 Publication	<1 %
28	Muhammad Yar, Sohail Shahzad, Lubna Shahzadi, Sohail Anjum Shahzad et al. "Heparin binding chitosan derivatives for production of pro-angiogenic hydrogels for	<1 %

promoting tissue healing", Materials Science and Engineering: C, 2017

Publication

29

Dhena Ria Barleany, Alpin Ilhami, Dea Yusuf Yudanto, Erizal. "Degradation Behaviour of Gamma Irradiated Poly(Acrylic Acid)-graft-Chitosan Superabsorbent Hydrogel", IOP Conference Series: Materials Science and Engineering, 2018

Publication

<1 %

30

Horia M. Nizam El-Din. "Synthesis and characterization of hydrogels based on gamma irradiation of acrylic acid and methacrylic acid", Polymer Composites, 2008

Publication

<1 %

31

[www.igi-global.com](http://www.igi-global.com)

Internet Source

<1 %

32

"Advanced Biopolymeric Systems for Drug Delivery", Springer Science and Business Media LLC, 2020

Publication

<1 %

33

Fabián Martínez-Gómez, Juan Guerrero, Betty Matsuhiro, Jorge Pavez. "Characterization of poly-d-mannuronate and poly-l-gulonate block fractions from sodium alginate and preparation of hydrogels with poly(vinylalcohol)", International Journal of Biological Macromolecules, 2018

<1 %

34

Li, Junjie, Liandong Deng, and Fanglian Yao.  
"Chitosan Derivatives", Chitosan-Based  
Hydrogels Functions and Applications, 2011.

Publication

---

<1 %

35

Zahra Shariatinia, Alireza Esmaeilzadeh.  
"Hybrid silica aerogel nanocomposite  
adsorbents designed for Cd(II) removal from  
aqueous solution", Water Environment  
Research, 2019

Publication

---

<1 %

36

[journalijdr.com](http://journalijdr.com)

Internet Source

---

<1 %

37

"Analytical Techniques in the Pharmaceutical  
Sciences", Springer Science and Business  
Media LLC, 2016

Publication

---

<1 %

38

Anna Karla dos S. Pereira, Davi T. Reis, Keleen  
M. Barbosa, Gessiel Newton Scheidt et al.  
"Antibacterial effects and ibuprofen release  
potential using chitosan microspheres loaded  
with silver nanoparticles", Carbohydrate  
Research, 2020

Publication

---

<1 %

39

Horia M. Nizam El-Din. "Gamma radiation  
synthesis and swelling properties of hydrogels  
based on poly(ethylene glycol)/methacrylic

<1 %

acid (MAc) mixtures", Journal of Applied Polymer Science, 07/15/2010

Publication

---

40

Lin Guo, Qing-Da An, Zuo-Yi Xiao, Shang-Ru Zhai, Li Cui. " Inherent N-Doped Honeycomb-like Carbon/Fe O Composites with Versatility for Efficient Microwave Absorption and Wastewater Treatment ", ACS Sustainable Chemistry & Engineering, 2019

Publication

---

<1 %

41

Nizam El-Din, Horia M.M., and Abdel Wahab M. El-Naggar. "Radiation synthesis of acrylic acid/polyethyleneimine interpenetrating polymer networks (IPNs) hydrogels and its application as a carrier of atorvastatin drug for controlling cholesterol", European Polymer Journal, 2012.

Publication

---

<1 %

42

Nuran Işıklan, Gülcan Küçükbalcı. "Microwave-induced synthesis of alginate-graft-poly(N-isopropylacrylamide) and drug release properties of dual pH- and temperature-responsive beads", European Journal of Pharmaceutics and Biopharmaceutics, 2012

Publication

---

<1 %

43

Serhat S. Çiçek, Tiffany Esposito, Ulrich Girreser. "Prediction of the sweetening effect of Siraitia grosvenorii (luo han guo) fruits by

<1 %

# two-dimensional quantitative NMR", Food Chemistry, 2021

Publication

44

Submitted to Vaal University of Technology

Student Paper

<1 %

45

Zahra Shariatinia, Zahra Zahraee. "Controlled release of metformin from chitosan-based nanocomposite films containing mesoporous MCM-41 nanoparticles as novel drug delivery systems", Journal of Colloid and Interface Science, 2017

Publication

<1 %

46

[mdpi-res.com](http://mdpi-res.com)

Internet Source

<1 %

47

"Polymers for Agri-Food Applications", Springer Science and Business Media LLC, 2019

Publication

<1 %

48

Oner, M.. "Ibuprofen release from porous hydroxyapatite tablets", Ceramics International, 201109

Publication

<1 %

49

[hdl.handle.net](http://hdl.handle.net)

Internet Source

<1 %

50

"Sustainable Agriculture Reviews 36", Springer Science and Business Media LLC, 2019

Publication

<1 %

51

Amit Kumar Nayak, Dilipkumar Pal, Kousik Santra. "Tamarind seed polysaccharide–gellan mucoadhesive beads for controlled release of metformin HCl", Carbohydrate Polymers, 2014

Publication

<1 %

52

Diany Elim, Andi Maqhfirah Nurul Fitri, Muhammad Alif Sya'ban Mahfud, Nur Afika et al. "Hydrogel forming microneedle-mediated transdermal delivery of sildenafil citrate from polyethylene glycol reservoir: An ex vivo proof of concept study", Colloids and Surfaces B: Biointerfaces, 2023

Publication

<1 %

53

Mengjie Sun, Ting Wang, Jianhui Pang, Xiguang Chen, Ya Liu. "Hydroxybutyl Chitosan Centered Biocomposites for Potential Curative Applications: A Critical Review", Biomacromolecules, 2020

Publication

<1 %

Exclude quotes On

Exclude matches Off

Exclude bibliography On