

# Encapsulation Red Ginger Oleoresin (*Zingiber officinale* var. *Rubrum*) With Chitosan- alginate as Wall Material Using Spray Drying

*by Dhena Ria Barleany*

---

**Submission date:** 04-Apr-2023 06:46PM (UTC+0700)

**Submission ID:** 2055563504

**File name:** msproof.pdf (299.81K)

**Word count:** 5616

**Character count:** 30514

## Research Article

### Encapsulation Red Ginger Oleoresin (*Zingiber officinale* var. *Rubrum*) With Chitosan-alginate as Wall Material Using Spray Drying

<sup>1</sup>Jayanudin, <sup>2</sup>Rahmadi, <sup>2</sup>Wiratni, <sup>1</sup>Meri Yulvianti, <sup>1</sup>Dhena Ria Barleany and <sup>1</sup>Widya Ernayati

<sup>1</sup>Department of Chemical Engineering, Faculty Engineering, Sultan Ageng Tirtayasa University  
Jl. Jenderal Sudirman km.03 Cilegon 42435, Indonesia

<sup>2</sup>Department of Chemical Engineering, Faculty Engineering, Gajah Mada University  
Jl. Grafika, No. 2, Yogyakarta 55281, Indonesia

**Abstract:** Encapsulation is the process of protecting the active ingredients that is susceptible to environmental influences by using a coating. Red ginger oleoresin contains bioactive components that can be used as natural antioxidants, but sensitive to environmental influence. Chitosan-alginate nanoparticle is used as the coating, because it is safe for consumption and also stable. The purpose of this research was to determine the effect of the Tripolyphosphate (TPP) concentration against the emulsion droplet size and determine the encapsulation efficiency of red ginger oleoresin. Encapsulation method was done by mixing 2% chitosan solution with 1% acetic acid, 1% sodium alginate and 8 g of red ginger oleoresin. The mixture was stirred and added sodium tripolyphosphate (3.5, 4.5 and 5.5%, respectively), emulsion preparation process was done by adding tween 80 (3, 4 and 5%, respectively) and then stirred using homogenizer with a speed of 22,000 rpm, emulsions formed were analyzed using nanoparticle analyzer. Emulsion formed was flowed on to the spray dryer inlet temperature of 180°C to form a powder encapsulation. Powder products were analyzed for determining encapsulation efficiency and morphology of red ginger oleoresin powder using Scanning Electron Microscopy (SEM). Based on the research results, the smallest droplet size of the emulsion was obtained at 481.5 nm and the largest encapsulation efficiency was as high as 70.59%.

**Keywords:** Chitosan, encapsulation, red ginger oleoresin, sodium alginate, tripolyphosphate

## INTRODUCTION

Ginger (*Zingiber officinale* var. *Rubrum*) is a plant that is used as spice in foods and pharmaceuticals in China, India and Arabic herbal traditions since ancient times as to treat inflammation, arthritis, neurological disease, gingivitis, asthma, stroke and diabetes, or antitumorigenic, diaphoretic, antispasmodic, expectorant (Ali *et al.*, 2008; Chrusasik *et al.*, 2005; Bellik, 2014; Kizhakkayil and Sasikumar, 2012). Characterization of ginger is pale yellow and flavorful spicy, ginger contains essential oils and oleoresins (Zarate and Yeoman, 1996; Bellik, 2014). The content of essential oil of ginger affects the aroma and produces a yield of 1-3% (Ali *et al.*, 2008; Kiran *et al.*, 2013; Eze and Agbo, 2011). El-Ghorab *et al.* (2010) said that the content of gingers essential oil about 1-4% depending on the type. In addition to essential oils, ginger also contains oleoresin about 4-7.5% (Zarate and Yeoman, 1996; Kiran *et al.*, 2013).

Red ginger (*Zingiber officinale* var. *Rubrum*) is part of the ginger varieties with spicier flavor. Rhizome size smaller with red leather. The phenol and flavonoid

content of red ginger is higher than the white ginger (*Zingiber officinale* Roscoe) (Oboh *et al.*, 2012). The antiradical activity of phenol and flavonoid based on the structure relationship between different parts of the chemical structure (Evans *et al.*, 1996). Sivasothy *et al.* (2011) have analyzed the essential oil of red ginger rhizome identified as many as 54 compounds. The oil was very rich in monoterpenoids (81.9%), comprising mainly camphene (14.5%), geranyl acetate (13.7%), geraniol (14.3%), nerol (7.7%), geraniol (7.3%) and 1, 8-cineole (5.0%). Red ginger also contains oleoresin which is a viscous liquid that resulting from extraction with organic solvents. Oleoresin contained bioactive components more than the essential oils because they contain volatile and non-volatile components (Onyeneke, 2000). Volatile component is contained in the essential oils and non-volatile components in oleoresin such as gingerol (Onyeneke, 2000; Lun *et al.*, 2008; Nwaoha *et al.*, 2013) and shogaol that formed from degradation of gingerol during heating or storage (Ali *et al.*, 2008; Bhattarai *et al.*, 2007; Wohlmut *et al.*, 2005). Red ginger oleoresin produce a yield of 13% resulting from

**Corresponding Author:** Jayanudin, Department of Chemical Engineering, Faculty Engineering, Sultan Ageng Tirtayasa University Jl. Jenderal Sudirman km.03 Cilegon 42435, Indonesia

This work is licensed under a Creative Commons Attribution 4.0 International License (URL: <http://creativecommons.org/licenses/by/4.0/>).

the extraction with ethanol, red ginger oleoresin analysis using GCMS can be detected as many as 45 compounds with the main compound is shogaol (11:22%) and zingerone (14:13%) (Jayanudin *et al.*, 2013).

Bioactive component contained in the oleoresin can be used as natural antioxidant and antimicrobial (El-Ghorab *et al.*, 2010; Oboh *et al.*, 2012; Sivasothy *et al.*, 2011; Yeh *et al.*, 2014; Dugasani *et al.*, 2010; Pawar *et al.*, 2011). Antioxidant activity of red ginger oleoresin is better than the others oleoresin and has the same activity with synthetic antioxidants (Singh *et al.*, 2008). The weakness of oleoresin is sensitive to light, heat and oxygen, so the bioactive components is easily degraded. It is caused by changes in polymer involving fatty oils and hydrocarbon components of monoterpenes (Balasubramani *et al.*, 2013; Shaikh *et al.*, 2006; Vaidya *et al.*, 2006). One solution of these problems is the encapsulation process (Jayanudin *et al.*, 2013; Vaidya *et al.*, 2006). Encapsulation is a coating technique of the active solid, liquid and gas using thin layer as wall material (Dubey *et al.*, 2009; Venkatesan *et al.*, 2009; Bansode *et al.*, 2010) Encapsulation is used to protect the bioactive compounds (polyphenols, micronutrients, enzyme, antioxidants and nutraceuticals) and also to control releasing at targeted sites (Gouin, 2004). Many research of the encapsulation process using alginate as wall material had been done (Bosio *et al.*, 2014; Santa-Maria *et al.*, 2012; El-Aassara *et al.*, 2014; Sathyabama *et al.*, 2014; Cook *et al.*, 2014; Oliveira *et al.*, 2014). Chitosan also had many uses for encapsulation processes (Wittayasuporn *et al.*, 2010; Trifkovic *et al.*, 2014; Koppolu *et al.*, 2014; Hosseini *et al.*, 2013; Jarudilokkul *et al.*, 2011; Al-Qadi *et al.*, 2012; Klaypradit and Huang, 2008; Choi *et al.*, 2013).

Coating for the encapsulation process used in this research was chitosan-alginate. The combination of the chitosan-alginate as wall material will have ionic bond to each other because of the difference ionic charges. Alginate bears the negative charges while chitosan bears the positive charge. Negative charge on the alginate is caused by the presence of carboxyl groups and positive charge of chitosan due to the presence of amino groups (Friedli and Schlager, 2005). The method used for the encapsulation process was spray drying. This method was more efficient to stabilize than a no capsule. The drying process is faster and the solid particles resulted will be more uniform. Encapsulation using spray drying depends also on the previous process as nano emulsion prior to spray drying (Ezhilarasi *et al.*, 2013). Another important factor is the effect of sodium tripolyphosphate concentration on the formation of cross-linked wall material of the encapsulation process. Spray drying is widely used in the encapsulation process (Nadeem *et al.*, 2013; Maciel *et al.*, 2014; Carvalho *et al.*, 2013; Torres *et al.*, 2013; Gallardo *et al.*, 2013; Borrmanna *et al.*, 2013; Anekella and Orsat, 2013; Kha *et al.*, 2014).

49  
The purposes of this research were to determine the effect of sodium tripolyphosphate concentration to the particle size of emulsion, to determine the encapsulation efficiency of the red ginger oleoresin with chitosan-alginate as wall material and to characterize the powder of red ginger oleoresin using Scanning Electron Microscope (SEM).

## MATERIALS AND METHODS

**Materials:** Red ginger oleoresin was obtained from CV. M and H Farm. Food grade chitosan was obtained from CV. Bio Chitosan Indonesia. MERCK™ n-Hexane p.a., MERCK™ Acetic Acid Glacial 100%, Tween 80 and Sodium tripolyphosphate was analytical grade from Merck.

**Emulsion preparation:** A solution of 2% chitosan was diluted with 1% acetic acid and mixed with 1% sodium alginate solution, then added 8 grams of red ginger oleoresin while stirring. In the Cross-link encapsulation process, a solution of tripolyphosphate with concentration (3.5, 4.5 and 5.5%, respectively) was added to the previous mixture and then stirred using homogenizer with a speed of 22,000 rpm and then tween 80 was added with concentration (3, 4 and 5%, respectively) to form emulsion. Emulsion droplets were analyzed using a nano size analyzer.

**Spray drying operation:** The emulsion was fed to a GEA Niro VERSATILE-SD™ spray dryer. The spray dryer was operated at inlet temperature is 180°C. The feed rate was adjusted to 1 L/h. The product of encapsulation was analyzed with Scanning Electron Microscopy (SEM) to get the morphology of microcapsule.

29  
**Encapsulation efficiency:** Encapsulation Efficiency (EE) was determined according to the method described by Bae and Lee (2008), *et al.* (2005) and Calvo *et al.* (2010). Ten milliliters of hexane was added to 3 g of powder and shake by hand for 2 min, at room temperature to extract free oil. The solvent mixture was then decanted and filtered through a Whatman No. 1 filter paper and after that, non-encapsulated oil (surface oil or free oil) was collected after distillation of hexane at 60°C. The non-encapsulated oil or free oil (surface oil) content was then calculated as percentage by the weight difference in the powder before and after extraction and washing with hexane. To measure the encapsulated oil (Total oil), oil was extracted by 4 h Soxhlet of the same powders. After that, hexane was evaporated and internal oil was scaled. Encapsulation Efficiency (EE) was calculated using the following formula:

$$(EE) = \frac{\text{Total oil} - \text{Surface oil}}{\text{Total oil}} \times 100\% \quad (1)$$

**Droplet size distribution:** The resulting droplet size from the emulsion process was analyzed using Nano Particle Analyzer (NPA) Brookhaven 90 plus, with the



following specifications: Size Range: 2 nm to 3  $\mu\text{m}$ , Diffusion Coefficient Range:  $10^{-6}$  to  $10^{-9}$   $\text{cm}^2/\text{sec}$ , Accuracy:  $\pm 1$  to 2% with monodisperse samples, Repeatability:  $\pm 1$  to 2% with dust free samples, Temperature Control (Optional): 5 to 75°C (22 steps of 0.1°C, Sample Volume: 3 mL, Results: Mean and Standard Deviation calculated for size distribution by weight assuming a Lognormal distribution.

**Scanning Electron Microscopy (SEM):** Powder morphology of the spray dryer products were analyzed using Scanning Electron Microscopy (SEM) JEOL-type JSM-6510LV in coated with a thin layer of platinum, resolution: high vacuum mode: 3.0 nm (30 kV) and Low Vacuum mode: 4.0 nm (30 kV), accelerating voltage: 0.5 to 30 kV. The SEM micrographs representing the microstructure of the powders were taken using software installed on a PC connected to the system.

## RESULTS AND DISCUSSION

**Droplet size:** Stages of encapsulation process started with the emulsion formation from a mixture of chitosan-alginate-TPP-Oleoresin of red ginger, emulsifier used is a non-ionic surfactant (tween 80). Emulsions are dispersion system of droplets of a liquid with another immiscible liquid. Emulsion droplet size can be divided into the microemulsion and nano emulsions, the difference lies in the effect of thermodynamic stability. Microemulsion is more stable than the nanoemulsion (McClements, 2011). Emulsifier used in this research is Tween 80 was a non-ionic surfactant because it produces better self-emulsifying formulations with faster emulsification time and smaller oil droplets in water (Eid *et al.*, 2012).

Figure 1 showed the effect of the Tripolyphosphate concentration (TPP) as cross-linked and tween 80 as emulsifier. The increase of the TPP concentration emulsion droplet size getting larger, at the fixed concentration of tween 80. For example Tween 80 at a concentration of 3% with TPP concentration of 3.5% obtained droplet size was 579.5 nm, the TPP concentration of 4.5% was 646.3 nm and TPP concentration of 5.5% was 768.2 nm. The same thing occur in the tween 80 concentration of 4 and 5%, generally droplet size increases with increasing concentration of TPP. The smallest droplet size obtained at tween 80 concentration of 5% and TPP concentration of 4.5% with a droplet size of 481.5 nm. Increasing droplet size of the emulsion of chitosan-alginate-TPP due to the present of cross-linked, so it is difficult to split into small droplets. Increasing the TPP concentration will cause aggregation in the mixture, so that the droplets become larger. Excess TPP may allow an increase in the formation of cross-linking that can lead to the formation of interparticle aggregation. The van der Waals forces are relatively weak attractive forces between atoms or nonpolar molecules, which

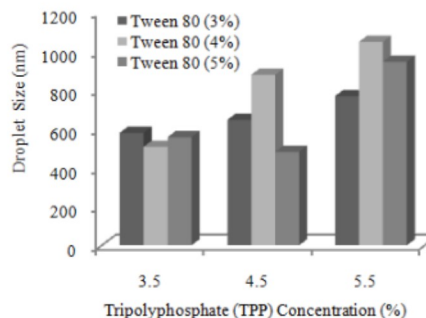


Fig. 1: The influence of TPP concentration on the droplet size of the emulsion at various concentrations of tween 80

increase as the molecular size increases (Jonassen *et al.*, 2012).

Tripolyphosphate (TPP) is a poly anion and can interact with cationic chitosan by electro static force. In addition, reversible physical cross linking by electrostatic interaction, instead of chemical cross linking, is applied to avoid possible toxicity of reagents and other undesirable effects. However, the mechanical strength of these chitosan beads is very poor, so its usage in the pharmaceutical industry is still limited (Liu and Zhu, 2000). TPP is the most extensively used ionic cross-linking agent, because of its non-toxic and multivalent properties (Shu and Zhu, 2002). Aral and Akbuga (1998) have strengthened TPP: chitosan beads by coating sodium alginate on the bead surface to form a polyelectrolyte complex film.

Aggregation is therefore suppressed when the local polymer concentration inside the nano particles is sufficiently high. On the other hand, electrostatic attraction between oppositely charged entities (such as chitosan and TPP) will promote aggregation (Jonassen *et al.*, 2012). Chitosan-TPP nanoparticles are formed by ionic gelation of Chitosan, a mechanism that is driven by the cross-linking of the Chitosan's  $-\text{NH}_3^+$  groups with the  $\text{P}_3\text{O}_{5,10}$  and  $\text{HP}_3\text{O}_{4,10}$  ionic species of TPP. The intra- and inter molecular linkages created between the negatively charged groups of TPP. In the presence of alginate, it is expected that the ionic gelation process occurs concomitantly with the complex of the polyelectrolyte with Alginate's  $-\text{COO}^-$  groups (Goycoolea *et al.*, 2009; Schatz *et al.*, 2004).

Illustration of emulsion droplet formation of red ginger oleoresin encapsulation process with chitosan-alginate coating in cross-linked with TPP using tween 80 as emulsifier modified from research of Schutz *et al.* (2011) could be seen in Fig. 2.

Emulsions are mixtures of two immiscible liquids, where one liquid dispersed as a droplet to another liquid due to the presence of a third substances as a stabilizer. Emulsifier concentration will affect the measurement of droplets Fig. 1 shows that in general the greater the concentration of Tween 80 droplet-droplet size becomes larger, it is related to the Critical Micelle Concentration (CMC), which shows the limits of the

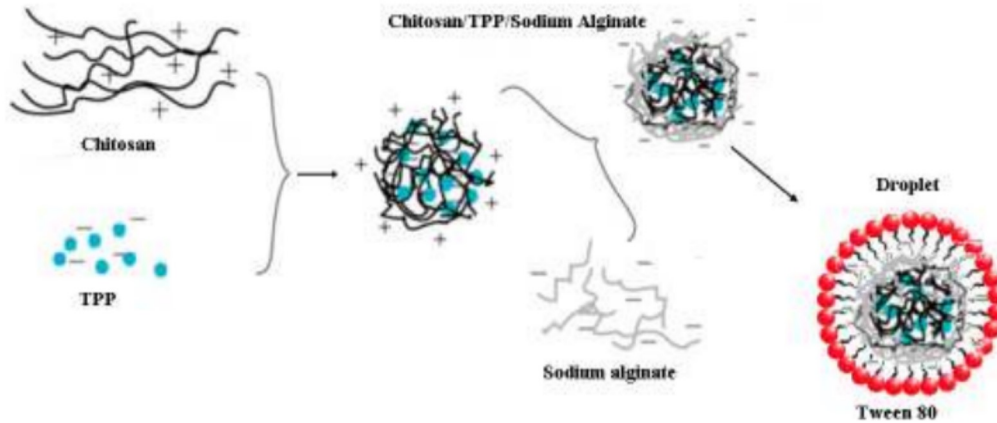


Fig. 2: Illustration of the formation of an emulsion droplet of red ginger oleoresin encapsulation with chitosan-alginate as wall material and cross-linked with TPP using emulsifier of tween 80

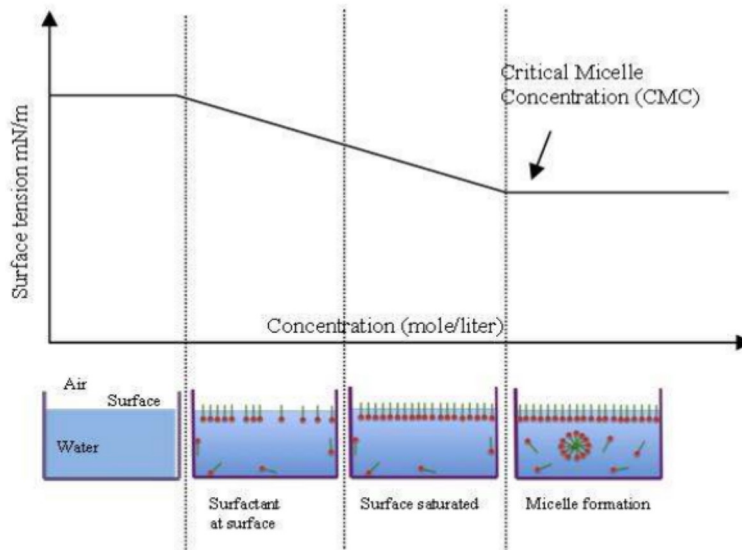


Fig. 3: Graph of critical micelle concentration

critical concentration of emulsifier in the solution, the greater concentration will be occur formation of micelle or aggregate (Picone and Cunha, 2013). As shown in Fig. 3.

**Encapsulation efficiency:** Encapsulation efficiency is determined by the number on the surface of red ginger oleoresin oil and total oil. Surfa<sup>39</sup>oil is the amount of red ginger oleoresin attached to the surface of the microcapsules and the total amount of oil is red ginger oleoresin contained in microcapsule, both contained in or attached to the surface of the microcapsules. Encapsulated efficiency can be seen in Table 1.

Table 1 showed changes in the concentration of TPP effect on the encapsulation efficiency. The greater

concentration of TPP leads to smaller encapsulation efficiency. The use of 5% tween 80 shows different trend, the encapsulation efficiency increases when concentration of TPP gets higher. The more tween 80 in the mixture leads to greater possibility of oleoresin aggregation and makes the oleoresin not coated, so that more oleoresin microcapsules attached to the surface and make the value of surface oil increase, as shown in Table 1. The Encapsulation Efficiency obtained in this experiment, approximately between 59.37-44.59%, is relatively low. It can be caused by the use of chitosan coating in cross-linked with TPP and alginate, so makes it more stable microcapsules. The increase concentration of TPP makes the total oil decreased and increasing surface oil makes encapsulation efficiency

Table 1: Encapsulation efficiency of red ginger oleoresin

| Tween 80 (%) | TPP (%) | Total oil (%) | Surface oil (%) | Encapsulation efficiency (%) |
|--------------|---------|---------------|-----------------|------------------------------|
| 3            | 3.5     | 10.30         | 3.30            | 67.74                        |
|              | 4.5     | 10.00         | 3.33            | 66.67                        |
|              | 5.5     | 10.00         | 4.00            | 60.00                        |
| 4            | 3.5     | 11.33         | 3.33            | 70.59                        |
|              | 4.5     | 9.67          | 3.33            | 65.52                        |
|              | 5.5     | 10.00         | 4.00            | 60.00                        |
| 5            | 3.5     | 10.67         | 4.33            | 59.37                        |
|              | 4.5     | 9.33          | 3.33            | 64.29                        |
|              | 5.5     | 6.67          | 2.67            | 60.00                        |

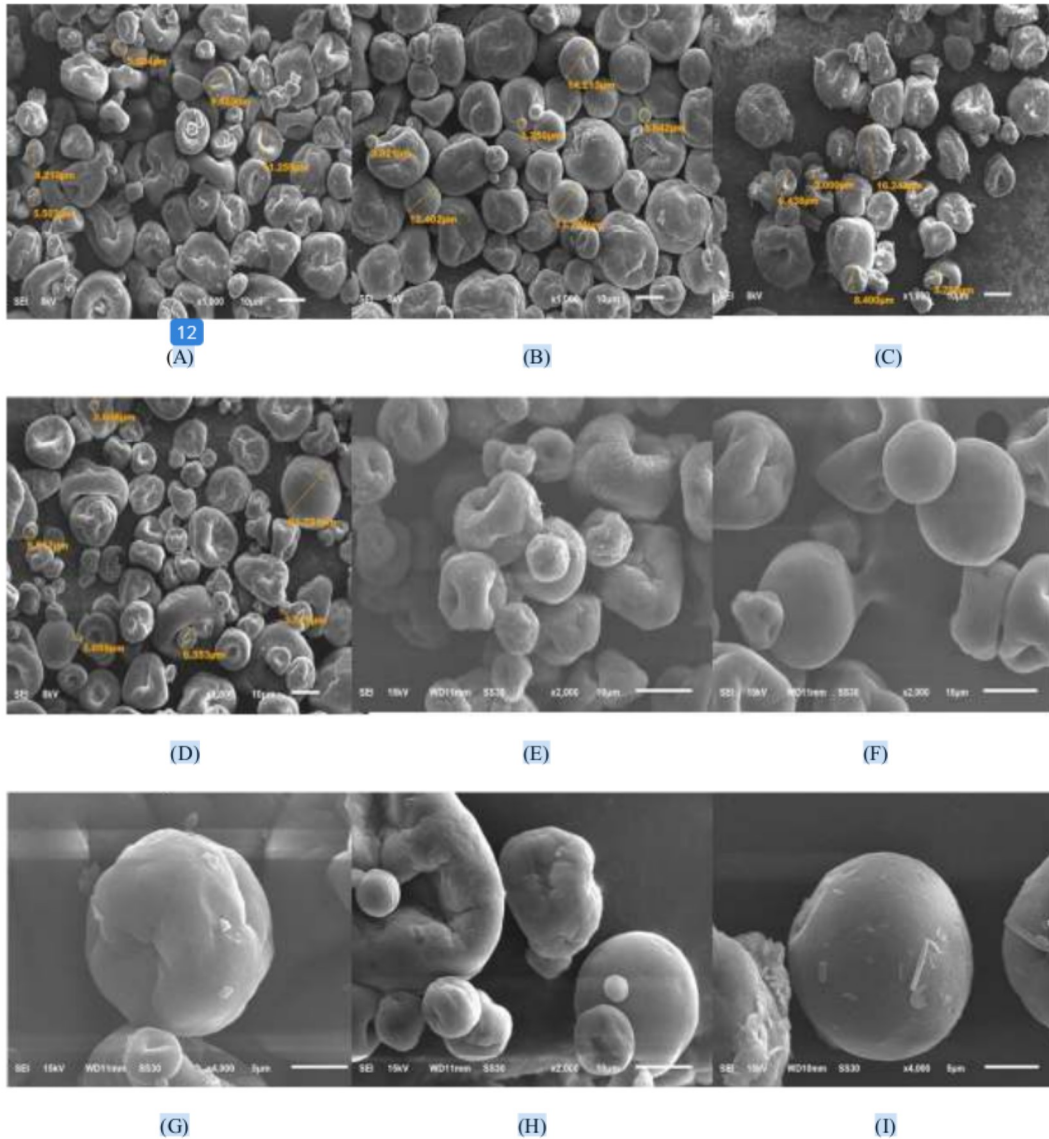


Fig. 4: SEM images of red ginger oleoresin with chitosan-alginate as wall; (A): Tween 80 (3%) TPP (3.5%); (B): Tween 80 (3%), TPP (4.5%); (C): Tween 80 (3%), TPP (5.5%); (D): Tween 80 (4%) TPP (3.5%); (E): Tween 80 (4%), TPP (4.5%); (F): Tween 80 (4%), TPP (5.5%); (G): Tween 80 (5%) TPP (3.5%); (H): Tween 80 (5%), TPP (4.5%); (I): Tween 80 (5%), TPP (5.5%)



value getting smaller. Increasing concentration of TPP will form aggregation, so that the red ginger oleoresin encapsulated decreased and resulted in non-encapsulated oleoresin attached to the surface of the microcapsules. Low Encapsulation Efficiency makes red ginger oleoresin more stick on the surface of microcapsule, so it will be easily oxidized due to direct contact with oxygen from the air (Aghbashlo *et al.*, 2012).

34  
The process of emulsification is an important role in determining the encapsulation efficiency especially for food flavors and oils (Liu *et al.*, 2000, 2001; Saberi *et al.*, 2014). Emulsion droplet size determines the encapsulation efficiency values at various core materials in the drying process (Sootitiantawat *et al.*, 2003, 2005). These reports clearly show that reducing emulsion size can result in encapsulated powders with higher retention of volatiles and lower content of encapsulated oil at the surface of powder particles. The presence of oil on the surface of the powder particles is the most undesirable property of encapsulated powders (Jafari *et al.*, 2008).

4  
**Powder morphology:** Microcapsules prepared by spray drying of red ginger oleoresin using chitosan-alginate as wall materials were observed for size and shape using the SEM (Fig. 4).

Figure 4 shows the morphology of ginger oleoresin microcapsules, in general, has a spherical shape with a smooth surface, except microcapsules A from Tween 80 (3%) TPP (3.5%), microcapsules produced almost all non-spherical shape. This can be caused by the imperfect process of cross-links between the chitosan-TPP in alginate coated, so that when it is passed to the spray dryer for the drying process, the wall material becomes brittle and microcapsule core here has no red ginger oleoresin. These phenomena can be seen from the analysis of red ginger oleoresin microcapsule morphology on the A. Red ginger oleoresin microcapsule size ranging from 2.0 to 14.21  $\mu\text{m}$ .

## CONCLUSION

Red ginger oleoresin encapsulation process with chitosan-alginate coating in cross-link with the TPP has been successfully done. Changes in the concentration of TPP as cross-link and tween 80 as emulsifier effect on emulsion droplet size, the smallest droplet size was obtained at a concentration of 4.5% TPP concentration and 4% tween 80 generated droplet size of 481.5 nm. The biggest of Encapsulation efficiency of red ginger oleoresin was 70.59% and the lowest was 59.7%, this value is still low because the coating of chitosan-alginate and cross-link with the TPP is stable on the mark with the amount of surface oil from the microcapsule obtained relatively small. Morphology of red ginger oleoresin microcapsules generally spherical shape with smooth surface, it indicates that the encapsulation process has been successfully done.

## ACKNOWLEDGMENT

9  
The authors are grateful to the Directorate of Higher Education Ministry of Education and Culture Republic of Indonesia through the Research Grant for providing financial support and also to Chemical Engineering Department of Sultan Ageng Tirtayasa University for providing laboratory facilities.

## REFERENCES

- Aghbashlo, M., H. Mobli, A. Madadlou and S. Rafiee, 2012. Influence of wall material and inlet drying air temperature on the microencapsulation of fish oil by spray drying. *Food Bioprocess Tech.*, 6(6): 1347-1356.
- Ali, B.H., G. Blunden, M.O. Tanira and A. Nemmar, 2008. Some phytochemical, pharmacological and toxicological properties of ginger (*Zingiber officinale* Roscoe): A review of recent research. *Food Chem. Toxicol.*, 46(2): 409-420.
- Al-Qadi, S., A. Grenha, D. Carrión-Recio, B. Seijo and C. Remuñán-López, 2012. Microencapsulated chitosan nanoparticles for pulmonary protein delivery: In vivo evaluation of insulin-loaded formulations. *J. Control. Release*, 157(3): 383-390.
- Anekella, K and V. Orsat, 2013. Optimization of microencapsulation of probiotics in raspberry juice by spray drying. *LWT-Food Sci. Technol.*, 50(1): 17-24.
- Aral, C. and J. Akbuga, 1998. Alternative approach to the preparation of chitosan beads. *Int. J. Pharm.*, 168(1): 9-15.
- Bae, E.K. and S.J. Lee, 2008. Microencapsulation of avocado oil by spray drying using whey protein and maltodextrin. *J. Microencapsul.*, 25(8): 549-560.
- Balasubramani, P., R. Viswanathan and M. Vairamani, 2013. Response surface optimisation of process variables for microencapsulation of garlic (*Allium sativum* L.) oleoresin by spray drying. *Biosyst. Eng.*, 114(3): 205-213.
- Bansode, S.S., S.K. Banarjee, S.L. Gaikwad, R. Jadhav and R.M. Thorat, 2010. Microencapsulation: A review. *Int. J. Pharm. Sci. Rev. Res.*, 1(1): 38-43.
- Bellik, Y., 2014. Total antioxidant activity and antimicrobial potency of the essential oil and oleoresin of *Zingiber officinale* roscoe. *Asian Pac. J. Trop. Dis.*, 4(1): 40-44.
- Bhattarai, S., V.H. Tran and C.C. Duke, 2007. Stability of [6]-gingerol and [6]-shogaol in simulated gastric and intestinal fluids. *J. Pharmaceut. Biomed.*, 45: 648-653.
- Borrmanna, D., A.P.T.R. Pierucci, S.G.F. Leite and M.H.M.R. Leao, 2013. Microencapsulation of passion fruit (*Passiflora*) juice with n-octenylsuccinate-derivatised starch using spray-drying. *Food Bioprod. Process.*, 91(1): 23-27.

- Bosio, V.E., S. Basu, F. Abdulla, M.E.C. Villalba, J.A. Guida, M. Arup and G.R. Castro, 2014. Encapsulation of Congo red in carboxymethyl guar gum-alginate gel microspheres. *React. Funct. Polym.*, 82: 103-110.
- Calvo, P., T. Hernández, M. Lozano and D.G. Gómez. 2010. Microencapsulation of extra-virgin olive oil by spray-drying: Influence of wall material and olive quality. *Eur. J. Lipid Sci. Tech.*, 112(8): 852-858.
- Carvalho, A.G.S., V.M. Silva and M.D. Hubinger, 2013. Microencapsulation by spray drying of emulsified green coffee oil with two-layered membranes. *Food Res. Int.*, 61: 236-245.
- Choi, J.S., Y. Kim, J. Kang, S.Y. Jeong and H.S. Yoo, 2013. Electrospun chitosan microspheres for complete encapsulation of anionic proteins: Controlling particle size and encapsulation efficiency. *AAPS PharmSciTech.*, 14(2): 794-801.
- Chrubasik, M.H., B.D. Pittler and Roufogalis, 2005. *Zingiberis rhizoma*: A comprehensive review on the ginger effect and efficacy profiles. *Phytomedicine*, 12(9): 684-701.
- Cook, M.T., G. Tzortzis, D. Charalampopoulos, V. Vitaliy and V.V. Khutoryanskiy, 2014. Microencapsulation of a synbiotic into PLGA/alginate multiparticulate gels. *Int. J. Pharm.*, 466(1-2): 400-408.
- Dubey, R., T.C. Shami and K.U.B. Rao, 2009. Microencapsulation technology and applications. *Defence Sci. J.*, 59(1): 82-95.
- Dugasani, S., M.R. Pichikac, V.D. Nadarajah, M.K. Balijepalli, S. Tandra and J.N. Korlakunta, 2010. Comparative antioxidant and anti-inflammatory effects of [6]-gingerol, [8]-gingerol, [10]-gingerol and [6]-shogaol. *J. Ethnopharmacol.*, 127(2): 515-520.
- Eid, A.M.M., S.H. Baie and O.M. Arafat, 2012. The effect of surfactant blends on the production of self-emulsifying system. *Int. J. Pharm. Frontier Res.*, 2(2): 21-31.
- El-Aassara, M.R., E.E. Hafezb, N.M. El-Deebc and M.M.G. Fouda, 2014. Microencapsulation of lectin anti-cancer agent and controlled release by alginate beads, biosafety approach. *Int. J. Biol. Macromol.*, 69: 88-94.
- El-Ghorab, A.H., M. Nauman, F.M. Anjum, S. Hussain and M. Nadeem, 2010. A comparative study on chemical composition and antioxidant activity of ginger (*Zingiber officinale*) and Cumin (*Cuminum cyminum*). *J. Agr. Food Chem.*, 58(14): 8231-8237.
- Evans, R.C., N.J. Miller and G. Paganga, 1996. Structure-antioxidant activity relationships of flavonoids and phenolic acids. *Free Radical Bio. Med.*, 20(7): 933-956.
- Eze, J.I. and K.E. Agbo, 2011. Comparative studies of sun and solar drying of peeled and unpeeled ginger. *Am. J. Sci. Ind. Res.*, 2(2): 136-143.
- Ezhilarasi, P.N., P. Karthik, N. Chhanwal and C. Anandharamakrishnan, 2013. Nan encapsulation techniques for food bioactive components: A review. *Food Bioprocess Tech.*, 6(3): 628-647.
- Friedli, A.C. and I.R. Schlager, 2005. Demonstrating encapsulation and release: A new take on alginate complexation and the nylon rope trick. *J. Chem. Educ.*, 82(7): 1017-1020.
- Gallardo, G., L. Guida, V. Martinez, M.C. López, D. Bernhardt, R. Blasco, R.P. Islas and L.G. Hermida, 2013. Microencapsulation of linseed oil by spray drying for functional food application. *Food Res. Int.*, 52(2): 473-482.
- Gouin, S., 2004. Microencapsulation: Industrial appraisal of existing technologies and trends. *Trends Food Sci. Tech.*, 15(7-8): 330-347.
- Goycoolea, F.M., G. Lollo, C.R. Lopez, F. Quaglia and M.J. Alonso, 2009. Chitosan-alginate blended nanoparticles as carriers for the transmucosal delivery of macromolecules. *Biomacromolecules*, 10(7): 1736-1743.
- Hosseini, S.F., M. Zandi, M. Rezaei and F. Farahmandghavi, 2013. Two-step method for encapsulation of oregano essential oil in chitosan nanoparticles: Preparation, characterization and in vitro release study. *Carbohydr. Polymers*, 95(1): 50-56.
- Jafari, S.M., E. Assadpoor, Y. He and B. Bhandari, 2008. Encapsulation efficiency of food flavours and oils during spray drying. *Dry. Technol.*, 26(7): 816-835.
- Jarudilokkul, S., A. Tongthammachat and V. Boonamnuayvittaya, 2011. Preparation of chitosan nanoparticles for encapsulation and release of protein. *Korean J. Chem. Eng.*, 28(5): 1247-1251.
- Jayanudin, R.B.D., Rochmadi, Wiratni, A. Sugiarti and Y.A. Kusuma, 2013. Modification on maceration extraction to the yield and components of red ginger oleoresin. *Proceeding of International Conference on Chemical Engineering. Parahyangan University*, pp: 72-77.
- Jonassen, H., A.L. Kjøniksen and M. Hiorth, 2012. Stability of chitosan nanoparticles cross-linked with tripolyphosphate. *Biomacromolecules*, 13(11): 3747-3756.
- Kha, T.C., M.H. Nguyen, P.D. Roach and C.E. Stathopoulos, 2014. Microencapsulation of Gac oil: Optimisation of spray drying conditions using response surface methodology. *Powder Technol.*, 264: 298-309.
- Kiran, C.R., A.K. Chakka, K.P.P. Amma, A.N. Menon, M.M.S. Kumar and V.V. Venugopalan, 2013. Influence of cultivar and maturity at harvest on the essential oil composition, oleoresin and [6]-Gingerol contents in fresh ginger from northeast India. *J. Agr. Food Chem.*, 61(17): 4145-4154.



- Kizhakkayil, J. and B. Sasikumar, 2012. Characterization of ginger (*Zingiber officinale* Rosc.) germplasm based on volatile and non-volatile components. *Afr. J. Biotechnol.*, 11(4): 777-786.
- Klaypradit, W. and Y.W. Huang, 2008. Fish oil encapsulation with chitosan using ultrasonic atomizer. *LWT-Food Sci. Technol.*, 41(6): 1133-1139.
- Koppolu, B.P., S.G. Smith, S. Ravindranathan, S. Jayanthi, T.K.S. Kumar and D.A. Zaharoff, 2014. Controlling chitosan-based encapsulation for protein and vaccine delivery. *Biomaterials*, 35(14): 4382-4389.
- Liu, X.D., T.T. Furuta, H. Yoshii and P. Linko, 2000. Retention of emulsified flavor in a single droplet during drying. *Food Sci. Technol. Res.*, 6: 335-339.
- Liu, X.D., T. Atarashi, T. Furuta, H. Yoshii, S. Aishima and M. Ohkawara, 2001. Microencapsulation of emulsified hydrophobic flavors by spray drying. *Dry. Technol.*, 19(7): 1361-1374.
- Lun, L.C., T. Derong and L. Le, 2008. Research on the extracting and anti-oxidation dynamic characteristics of ginger oleoresin. *Int. J. Food Sci. Tech.*, 43(3): 517-525.
- Maciel, G.M., K.S. Chaves, C.R.F. Grosso and M.L. Gigante, 2014. Microencapsulation of *Lactobacillus acidophilus* La-5 by spray-drying using sweet whey and skim milk as encapsulating materials. *J. Dairy Sci.*, 97(4): 1991-1998.
- McClements, D.J., 2011. Edible nanoemulsions: Fabrication, properties and functional performance. *Soft Matter*, 7(6): 2297-2316.
- Nadeem, H.S., C. Dinçer, M. Torun, A. Topuz and F. Özdemir, 2013. Influence of inlet air temperature and carrier material on the production of instant soluble sage (*Salvia fruticosa* Miller) by spray drying. *LWT-Food Sci. Technol.*, 52(1): 31-38.
- Nwaoha, M., I. Elizabeth, Okafor, G. Ifeanyi and A.O. Veronica, 2013. Production of oleoresin from ginger (*Zingiber officinale*) peels and evaluation of its antimicrobial and antioxidative properties. *Afr. J. Microbiol. Res.*, 7(42): 4981-4989.
- Oboh, G., J.A. Ayodele and O.A. Adedayo, 2012. Antioxidant and inhibitory effect of red ginger (*Zingiber officinale* var. *Rubra*) and white ginger (*Zingiber officinale* Roscoe) on Fe<sup>2+</sup> induced lipid peroxidation in rat brain in vitro. *Exp. Toxicol. Pathol.*, 64(1-2): 31-36.
- Oliveira, E.F., H.C.B. Paulaa and R.C.M. de Paula, 2014. Alginate/cashew gum nanoparticles for essential oil encapsulation. *Colloid. Surface. B*, 113: 146-151.
- Onyenekwe, P.C., 2000. Assessment of oleoresin and gingerol contents in gamma irradiated ginger rhizomes. *Mol. Nutr. Food Res.*, 44(2): 130-132.
- Pawar, N., S. Pai, M. Nimbalkar and G. Dixit, 2011. RP-HPLC analysis of phenolic antioxidant compound 6-gingerol from different ginger cultivars. *Food Chem.*, 126(3): 1330-1336.
- Picone, C.S.F. and R.L. Cunha, 2013. Formation of nano and microstructures by polysorbate-chitosan association. *Colloid. Surface. A*, 418: 29-38.
- Saberi, M., M. Hashemiravan and N. Farhadyar, 2014. Influence of casein and inulin on the properties of nano-particle encapsulation of fish oil. *J. Biodiversity Environ. Sci.*, 4(2): 318-326.
- Santa-Maria, M., H. Scher and T. Jeoh, 2012. Microencapsulation of bioactives in cross-linked alginate matrices by spray drying. *J. Microencapsul.*, 29(3): 286-295
- Sathyabama, S., M.R. Kumar, P.B. Devi, R. Vijayabharathi and V.B. Priyadharisini, 2014. Co-encapsulation of probiotics with prebiotics on alginate matrix and its effect on viability in simulated gastric environment. *LWT-Food Sci. Technol.*, 57(1): 419-425.
- Schatz, C., A. Domard, C. Viton, C. Pichot and T. Delair, 2004. Versatile and efficient formation of colloids of biopolymer-based polyelectrolyte complexes. *Biomacromolecules*, 5(5): 1882-1892.
- Schutz, C.A., L.J. Jeanneret, P. Käuper and C. Wandrey, 2011. Cell response to the exposure to chitosan-TPP//alginate nanogels. *Biomacromolecules*, 12: 4153-4161.
- Shaikh, J., R. Bhosale and R. Singhal, 2006. Microencapsulation of black pepper oleoresin. *Food Chem.*, 94(1): 105-110.
- Shu, X.Z. and K.J. Zhu, 2000. A novel approach to prepare tripolyphosphate: Chitosan complex beads for controlled release drug delivery. *Int. J. Pharm.*, 201(1): 51-58.
- Shu, X.Z. and K.J. Zhu, 2002. Controlled drug release properties of ionically cross-linked chitosan beads: The influence of anion structure. *Int. J. Pharm.*, 233: (1-2): 217-225.
- Singh, G., I.P.S. Kapoor, P. Singh, C.S. de Heluani, M.P. de Lampasona and C.A.N. Catalan, 2008. Chemistry, antioxidant and antimicrobial investigations on essential oil and oleoresins of *Zingiber officinale*. *Food Chem. Toxicol.*, 46(10): 3295-3302.
- Sivasothy, Y., W.K. Chong, A. Hamid, I.M. Eldeen, S.F. Sulaiman and K. Awang, 2011. Essential oils of *Zingiber officinale* var. *rubrum* Theilade and their antibacterial activities. *Food Chem.*, 124(2): 514-517.
- Soottitantawat, A., H. Yoshii, T. Furuta, M. Ohkawara and P. Linko, 2003. Microencapsulation by spray drying: Influence of emulsion size on the retention of volatile compounds. *J. Food Sci.*, 68(7): 2256-2262.

- Soottitawat, A., F. Bigeard, H. Yoshii, T. Furuta, M. Ohkawara and P. Linko, 2005. Influence of emulsion and powder size on the stability of encapsulated D-limonene by spray drying. *Innov. Food Sci. Emerg.*, 6(1): 107-114.
- Tan, L.H., L.W. Chan and P.W.S. Heng, 2005. Effect of oil loading on microspheres produced by spray drying. *J. Microencapsul.*, 22(3): 253-259.
- Torres, L.M., E.E. García-Cruz, F. Calderas, R.F.G. Laredo, G.S. Olivares, J.A.G. Infante, N.E.R. Guzmán and J.R. Ramírez, 2013. Microencapsulation by spray drying of gallic acid with nopal mucilage (*Opuntia ficus indica*). *LWT-Food Sci. Technol.*, 50(2): 642-650.
- Trifkovic, K.T., N.Z. Milasinovic, V.B. Djordjevic, M.T.K. Krusic, D. Zorica, K. Jugovic, V.A. Nedovic and B.M. Bugarskia, 2014. Chitosan microbeads for encapsulation of thyme (*Thymus serpyllum* L.) polyphenols. *Carbohydr. Polym.*, 111: 901-907.
- Vaidya, S., R. Bhosale and R.S. Singhal, 2006. Microencapsulation of cinnamon oleoresin by spray drying using different wall materials. *Dry. Technol.*, 24(8): 983-992.
- Venkatesan, P., R. Manavalan and K. Valliappan, 2009. Microencapsulation: A vital technique in novel drug delivery system. *J. Pharm. Sci. Res.*, 1(4): 26-32.
- Wittayasuporn, M., S. Rengpipat, T. Palaga, P. Asawanonda, N. Anumansirikul and S.P. Wanichwecharungruang, 2010. Chitosan derivative nanocarrier: Safety evaluation, antibacterial property and ascorbyl palmitate encapsulation. *J. Microencapsul.*, 27(3): 218-225.
- Wohlmuth, H., D.N. Leach, M.K. Smith and S. Myers, 2005. Gingerol content of diploid and tetraploid clones of ginger (*Zingiber officinale* Roscoe). *J. Agr. Food Chem.*, 53(14): 5772-5778.
- Yeh, H.Y., C.H. Chuang, H.C. Chen, C.J. Wan, T.L. Chen and L.Y. Lin, 2014. Bioactive components analysis of two various gingers (*Zingiber officinale* Roscoe) and antioxidant effect of ginger extracts. *LWT-Food Sci. Technol.*, 55(1): 329-334.
- Zarate, R. and R.R. Yeoman, 1996. Changes in the amounts of [6] gingerol and derivatives during a culture cycle of ginger, *Zingiber officinale*. *Plant Sci.*, 121(1): 115-122.

# Encapsulation Red Ginger Oleoresin (*Zingiber officinale* var. *Rubrum*) With Chitosan-alginate as Wall Material Using Spray Drying

## ORIGINALITY REPORT

**22%**  
SIMILARITY INDEX

**15%**  
INTERNET SOURCES

**19%**  
PUBLICATIONS

**7%**  
STUDENT PAPERS

## PRIMARY SOURCES

- 1** Biswas, A.K.. "Studies on environmental quality in and around municipal solid waste dumpsite", *Resources, Conservation & Recycling*, 201012  
Publication 1%
- 2** [coek.info](#)  
Internet Source 1%
- 3** [link.springer.com](#)  
Internet Source 1%
- 4** Krishnan, S.. "The use of gum arabic and modified starch in the microencapsulation of a food flavoring agent", *Carbohydrate Polymers*, 20051214  
Publication 1%
- 5** [technodocbox.com](#)  
Internet Source 1%
- 6** Hilman Ibnu Mahdi, Eka Irawan, N. Nuryoto, J. Jayanudin, Hary Sulisty, Wahyudi Budi 1%



Sediawan, Oki Muraza. "Glycerol Carbonate Production from Biodiesel Waste Over Modified Natural Clinoptilolite", Waste and Biomass Valorization, 2016

Publication

---

7 Surashree Sen Gupta, Santinath Ghosh, Prabir Maiti, Mahua Ghosh. "Microencapsulation of conjugated linolenic acid-rich pomegranate seed oil by an emulsion method", Food Science and Technology International, 2012

Publication

---

8 Submitted to Universiti Sains Islam Malaysia

Student Paper

---

9 [pubs.sciepub.com](http://pubs.sciepub.com)

Internet Source

---

10 Submitted to Universitas Muhammadiyah Surakarta

Student Paper

---

11 [www.kosfaj.org](http://www.kosfaj.org)

Internet Source

---

12 [docksci.com](http://docksci.com)

Internet Source

---

13 Wunwisa Krasaekoopt. "Influence of Non-Equilibrium States and Glass Transition on the Survival of Bacteria", Elsevier BV, 2017

Publication

---

14 Atif Sarwar, Haliza Katas, Noraziah Mohamad Zin. "Antibacterial effects of chitosan-tripolyphosphate nanoparticles: impact of particle size molecular weight", Journal of Nanoparticle Research, 2014  
Publication <1 %

---

15 [etd.repository.ugm.ac.id](http://etd.repository.ugm.ac.id)  
Internet Source <1 %

---

16 [norcaloa.com](http://norcaloa.com)  
Internet Source <1 %

---

17 [vdoc.pub](http://vdoc.pub)  
Internet Source <1 %

---

18 P. N. Ezhilarasi, P. Karthik, N. Chhanwal, C. Anandharamakrishnan. "Nanoencapsulation Techniques for Food Bioactive Components: A Review", Food and Bioprocess Technology, 2012  
Publication <1 %

---

19 Erlina Yustanti, Alfian Noviyanto, Laila Chusnul Chotimah, Muhamad Abdur Rais Saputra, Maulana Randa, Maykel Manawan. "Increased Electromagnetic Wave Absorption through Controlled Sonication Processing on BaFe<sub>11.2</sub>Mg<sub>0.4</sub>Al<sub>0.4</sub>O<sub>19</sub> Nanoparticles", Coatings, 2022  
Publication <1 %

---

Submitted to University of Birmingham

20

Student Paper

&lt;1 %

21

[aspace.agrif.bg.ac.rs](http://aspace.agrif.bg.ac.rs)

Internet Source

&lt;1 %

22

[pure.rug.nl](http://pure.rug.nl)

Internet Source

&lt;1 %

23

[www.aensiweb.com](http://www.aensiweb.com)

Internet Source

&lt;1 %

24

Abedalghani Halahlah, Vieno Piironen, Kirsi S. Mikkonen, Thao M. Ho. "Polysaccharides as wall materials in spray-dried microencapsulation of bioactive compounds: Physicochemical properties and characterization", *Critical Reviews in Food Science and Nutrition*, 2022

Publication

&lt;1 %

25

Submitted to King Saud University

Student Paper

&lt;1 %

26

Lucie Chocholoušová Havlíková, Martina Urbanová, Petr Chocholouš, Petr Solich. "Novel Dispersed Sorbent Sorptive Extraction Method for the Chromatography Profiling of Active Substances in Ginger", *Food Analytical Methods*, 2016

Publication

&lt;1 %

27

Submitted to University of Sheffield

Student Paper



<1 %

28

[1library.net](https://1library.net)

Internet Source

<1 %

29

[www.degruyter.com](https://www.degruyter.com)

Internet Source

<1 %

30

Ssemwanga Mohammed, Nakiguli Fatumah, Nasejje Shadia. "Drying performance and economic analysis of novel hybrid passive-mode and active-mode solar dryers for drying fruits in East Africa", Journal of Stored Products Research, 2020

Publication

<1 %

31

Mortaza Aghbashlo, Hossien Mobli, Ashkan Madadlou, Shahin Rafiee. "Influence of Wall Material and Inlet Drying Air Temperature on the Microencapsulation of Fish Oil by Spray Drying", Food and Bioprocess Technology, 2012

Publication

<1 %

32

Wang, A.j.. "Effect of process parameters on the performance of spray dried hydroxyapatite microspheres", Powder Technology, 20090404

Publication

<1 %

33

[www.mdpi.com](https://www.mdpi.com)

Internet Source

<1 %

34

Encina, Cristian, Cristina Vergara, Begoa Giménez, Felipe Oyarzún-Ampuero, and Paz Robert. "Conventional spray-drying and future trends for the microencapsulation of fish oil", *Trends in Food Science & Technology*, 2016.

Publication

&lt;1 %

35

Simon-Brown, Kelly, Kevin Mis Solval, Aranee Chotiko, Luis Alfaro, Vondel Reyes, Chen Liu, Bennett Dzandu, Emmanuel Kyereh, Andrea Goldson Barnaby, Ian Thompson, Zhimin Xu, and Subramaniam Sathivel.

"Microencapsulation of ginger (*Zingiber officinale*) extract by spray drying technology", *LWT - Food Science and Technology*, 2016.

Publication

&lt;1 %

36

[etd.auburn.edu](http://etd.auburn.edu)

Internet Source

&lt;1 %

37

B A Larasati, B Panunggal, D N Afifah, G Anjani, N Rustanti. " Total lactic acid bacteria, antioxidant activity, and acceptance of synbiotic yoghurt with red ginger extract ( ) ", *IOP Conference Series: Earth and Environmental Science*, 2018

Publication

&lt;1 %

38

Hongcai Zhang, Miaomiao Feng, Yapeng Fang, Yan Wu, Yuan Liu, Yanyun Zhao, Jianxiong Xu. "Recent advancements in encapsulation of chitosan-based enzymes and their

&lt;1 %

applications in food industry", Critical Reviews  
in Food Science and Nutrition, 2022

Publication

39

Ismail Tontul, Ayhan Topuz.

"Microencapsulation of Plant Oils Rich in  
Alpha-Linolenic Acid", Elsevier BV, 2015

Publication

<1 %

40

Kizhakkayil Jaleel, Sasikumar B.

"Characterization of ginger (*Zingiber officinale*  
Rosc.) germplasm based on volatile and non-  
volatile components", African Journal of  
Biotechnology, 2012

Publication

<1 %

41

Taruna Syah, Ikrar, Purnama Darmadji, and

Yudi Pranoto. "Microencapsulation of Refined  
Liquid Smoke Using Maltodextrin Produced  
from Broken Rice Starch : Microencapsulation  
of Refined Liquid Smoke", Journal of Food  
Processing and Preservation, 2016.

Publication

<1 %

42

catbull.com

Internet Source

<1 %

43

docplayer.net

Internet Source

<1 %

44

eprints.hud.ac.uk

Internet Source

<1 %

etheses.whiterose.ac.uk



45

Internet Source

&lt;1 %

46

[jnfs.ssu.ac.ir](http://jnfs.ssu.ac.ir)

Internet Source

&lt;1 %

47

[ogma.newcastle.edu.au](http://ogma.newcastle.edu.au)

Internet Source

&lt;1 %

48

[tesionline.unicatt.it](http://tesionline.unicatt.it)

Internet Source

&lt;1 %

49

[www.gjasr.com](http://www.gjasr.com)

Internet Source

&lt;1 %

50

Dash, M.. "Chitosan-A versatile semi-synthetic polymer in biomedical applications", Progress in Polymer Science, 201108

Publication

&lt;1 %

51

Seid Mahdi Jafari, Elham Assadpoor, Yinghe He, Bhesh Bhandari. "Encapsulation Efficiency of Food Flavours and Oils during Spray Drying", Drying Technology, 2008

Publication

&lt;1 %

52

T. K. Lim. "Edible Medicinal and Non-Medicinal Plants", Springer Nature, 2016

Publication

&lt;1 %

53

Basak Yazicioglu, Serpil Sahin, Gulum Sumnu. "Microencapsulation of wheat germ oil", Journal of Food Science and Technology, 2014

Publication

&lt;1 %

54

Samira Shamaei, Seyed Sadegh Seiedlou,  
Mortaza Aghbashlo, Hadi Valizadeh.

<1 %

"Mathematical modeling of drying behavior of  
single emulsion droplets containing functional  
oil", Food and Bioproducts Processing, 2017

Publication

---

Exclude quotes On

Exclude matches Off

Exclude bibliography On

# Encapsulation Red Ginger Oleoresin (Zingiber officinale var. Rubrum) With Chitosan-alginate as Wall Material Using Spray Drying

---

GRADEMARK REPORT

---

FINAL GRADE

**/0**

GENERAL COMMENTS

**Instructor**

---

PAGE 1

---

PAGE 2

---

PAGE 3

---

PAGE 4

---

PAGE 5

---

PAGE 6

---

PAGE 7

---

PAGE 8

---

PAGE 9

---